

**CIHM
Microfiche
Series
(Monographs)**

**ICMH
Collection de
microfiches
(monographies)**



Canadian Institute for Historical Microreproductions / Institut canadien de microreproductions historiques

© 1997

Technical and Bibliographic Notes / Notes techniques et bibliographiques

The Institute has attempted to obtain the best original copy available for filming. Features of this copy which may be bibliographically unique, which may alter any of the images in the reproduction, or which may significantly change the usual method of filming are checked below.

- ☒ Coloured covers / Couverture de couleur
- ☐ Covers damaged / Couverture endommagée
- ☐ Covers restored and/or laminated / Couverture restaurée et/ou pelliculée
- ☐ Cover title missing / Le titre de couverture manque
- ☒ Coloured maps / Cartes géographiques en couleur
- ☐ Coloured ink (i.e. other than blue or black) / Encre de couleur (i.e. autre que bleue ou noire)
- ☐ Coloured plates and/or illustrations / Planches et/ou illustrations en couleur
- ☐ Bound with other material / Relié avec d'autres documents
- ☐ Only edition available / Seule édition disponible
- ☐ Tight binding may cause shadows or distortion along interior margin / La reliure serrée peut causer de l'ombre ou de la distorsion le long de la marge intérieure.
- ☐ Blank leaves added during restorations may appear within the text. Whenever possible, these have been omitted from filming / Il se peut que certaines pages blanches ajoutées lors d'une restauration apparaissent dans le texte, mais, lorsque cela était possible, ces pages n'ont pas été filmées.
- ☒ Additional comments / Commentaires supplémentaires:
- Various pagings.

L'Institut a microfilmé le meilleur exemplaire qu'il lui a été possible de se procurer. Les détails de cet exemplaire qui sont peut-être uniques du point de vue bibliographique, qui peuvent modifier une image reproduite, ou qui peuvent exiger une modification dans la méthode normale de filmage sont indiqués ci-dessous.

- ☐ Coloured pages / Pages de couleur
- ☐ Pages damaged / Pages endommagées
- ☐ Pages restored and/or laminated / Pages restaurées et/ou pelliculées
- ☒ Pages discoloured, stained or foxed / Pages décolorées, tachetées ou piquées
- ☐ Pages detached / Pages détachées
- ☒ Showthrough / Transparence
- ☐ Quality of print varies / Qualité inégale de l'impression
- ☐ Includes supplementary material / Comprend du matériel supplémentaire
- ☐ Pages wholly or partially obscured by errata slips, tissues, etc., have been refilmed to ensure the best possible image / Les pages totalement ou partiellement obscurcies par un feuillet d'errata, une pelure, etc., ont été filmées à nouveau de façon à obtenir la meilleure image possible.
- ☐ Opposing pages with varying colouration or discolourations are filmed twice to ensure the best possible image / Les pages s'opposant ayant des colorations variables ou des décolorations sont filmées deux fois afin d'obtenir la meilleure image possible.

**This item is filmed at the reduction ratio checked below /
Ce document est filmé au taux de réduction indiqué ci-dessous.**

A horizontal number line with 16 equal segments. The top of the line is labeled with $10x$, $14x$, $18x$, $22x$, $26x$, and $30x$. The bottom of the line is labeled with $12x$, $16x$, $20x$, $24x$, $28x$, and $32x$. A checkmark is placed above the 10th segment from the left, which corresponds to the $24x$ mark.

The copy filmed here has been reproduced thanks to the generosity of:



National Library of Canada

The images appearing here are the best quality possible considering the condition and legibility of the original copy and in keeping with the filming contract specifications.

Original copies in printed paper covers are filmed beginning with the front cover and ending on the last page with a printed or illustrated impression, or the back cover when appropriate. All other original copies are filmed beginning on the first page with a printed or illustrated impression, and ending on the last page with a printed or illustrated impression.

The last recorded frame on each microfiche shall contain the symbol $\longrightarrow$ (meaning "CONTINUED"), or the symbol ∇ (meaning "END"), whichever applies.

Maps, plates, charts, etc., may be filmed at different reduction ratios. Those too large to be entirely included in one exposure are filmed beginning in the upper left hand corner, left to right and top to bottom, as many frames as required. The following diagrams illustrate the method:

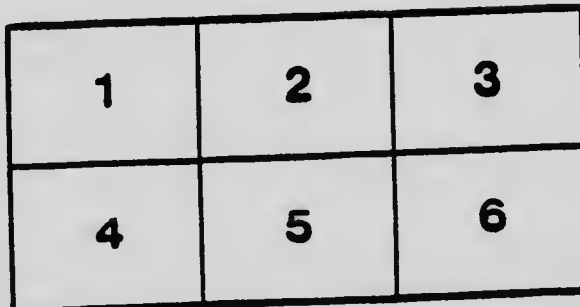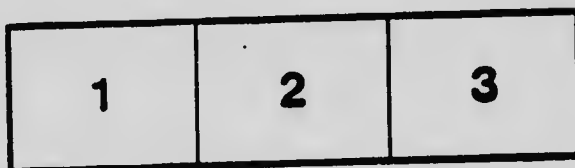

L'exemplaire filmé fut reproduit grâce à la générosité de:


Bibliothèque nationale du Canada

Les images suivantes ont été reproduites avec le plus grand soin, compte tenu de la condition et de la netteté de l'exemplaire filmé, et en conformité avec les conditions du contrat de filmage.

Les exemplaires originaux dont la couverture en papier est imprimée sont filmés en commençant par le premier plat et en terminant soit par la dernière page qui comporte une empreinte d'impression ou d'illustration, soit par le second plat, selon le cas. Tous les autres exemplaires originaux sont filmés en commençant par la première page qui comporte une empreinte d'impression ou d'illustration et en terminant par la dernière page qui comporte une telle empreinte.


Un des symboles suivants apparaîtra sur la dernière image de chaque microfiche, selon le cas: le symbole $\longrightarrow$ signifie "A SUIVRE", le symbole ∇ signifie "FIN".

Les cartes, planches, tableaux, etc., peuvent être filmés à des taux de réduction différents. Lorsque le document est trop grand pour être reproduit en un seul cliché, il est filmé à partir de l'angle supérieur gauche, de gauche à droite, et de haut en bas, en prenant le nombre d'images nécessaire. Les diagrammes suivants illustrent la méthode.

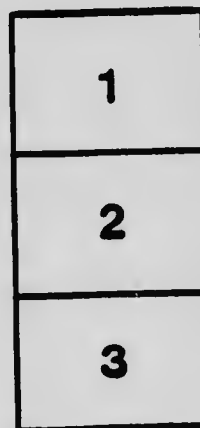

MICROCOPY RESOLUTION TEST CHART

(ANSI and ISO TEST CHART No. 2)

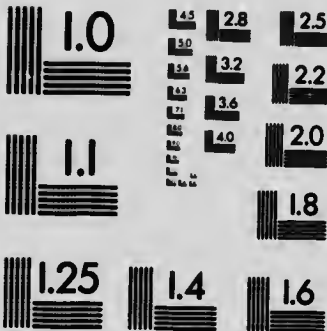

APPLIED IMAGE Inc

1653 East Main Street
Rochester, New York 14609 USA
(716) 482-0300 - Phone
(716) 286-5989 - Fax

M32-105

CANADA
DEPARTMENT OF MINES
HON. LOUIS CORDERO, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER.
MINES BRANCH
EUGENE HAANEL, Ph.D., DIRECTOR.

AUSTIN BROOK IRON-BEARING DISTRICT
NEW BRUNSWICK

BY
EINAR LINDEMAN, M.E.



OTTAWA
GOVERNMENT PRINTING BUREAU
1913

No. 106.

CANADA
DEPARTMENT OF MINES
HON. LOUIS CORDERRE, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER.
MINES BRANCH
EUGENE HAANEL, PH.D., DIRECTOR.

AUSTIN BROOK IRON-BEARING DISTRICT
NEW BRUNSWICK

BY
EINAR LINDEMAN, M.E.



OTTAWA
GOVERNMENT PRINTING BUREAU
1913

13223—1

No. 105.

Dr. EUGENE HAANEL,
Director of Mines Branch,
Department of Mines,
Ottawa.

SIR,—I beg to submit, herewith, the following report
on work done in the Austin Brook iron-bearing district.

I have the honour to be, Sir,
Your obedient servant,

(Signed) E. Lindeman.

Ottawa, March 1, 1911.

CONTENTS.

	PAGE.
Introductory.....	1
Field work.....	1
Location and area.....	1
History.....	2
Geology.....	3
Character of ore.....	3
Analysis.....	4
Diamond drill records.....	6
Distribution of ore bodies.....	9
Extent of ore bodies.....	10
Mining operations.....	11
Description of concentrating mill.....	11

ILLUSTRATIONS.

PHOTOGRAPHS.

PLATE	I. Austin Brook mining camp, N.B.....	1
	II. Open-cut on No. 1 deposit at Austin Brook, N.B.....	8
	III. Concentrating mill at Austin Brook, N.B.....	10

DRAWINGS.

No.	1. Sections of diamond drill holes.....	5
"	2. Flow sheet of concentrating plant at Austin Brook.....	13
"	3. General lay-out of concentrating plant at Austin Brook, N.B.....	15
"	4. Plan of concentrating mill at Austin Brook, N.B.....	Following
"	5. Section of " " " " " " " ".....	Following

MAPS.

No.	106. Geological map of Austin Brook iron-bearing district, N.B.....	End
"	107. Magnetometric map of Austin Brook iron-bearing district, N.B.....	"
"	108. Index map showing location of Austin Brook iron-bearing district, N.B..	"


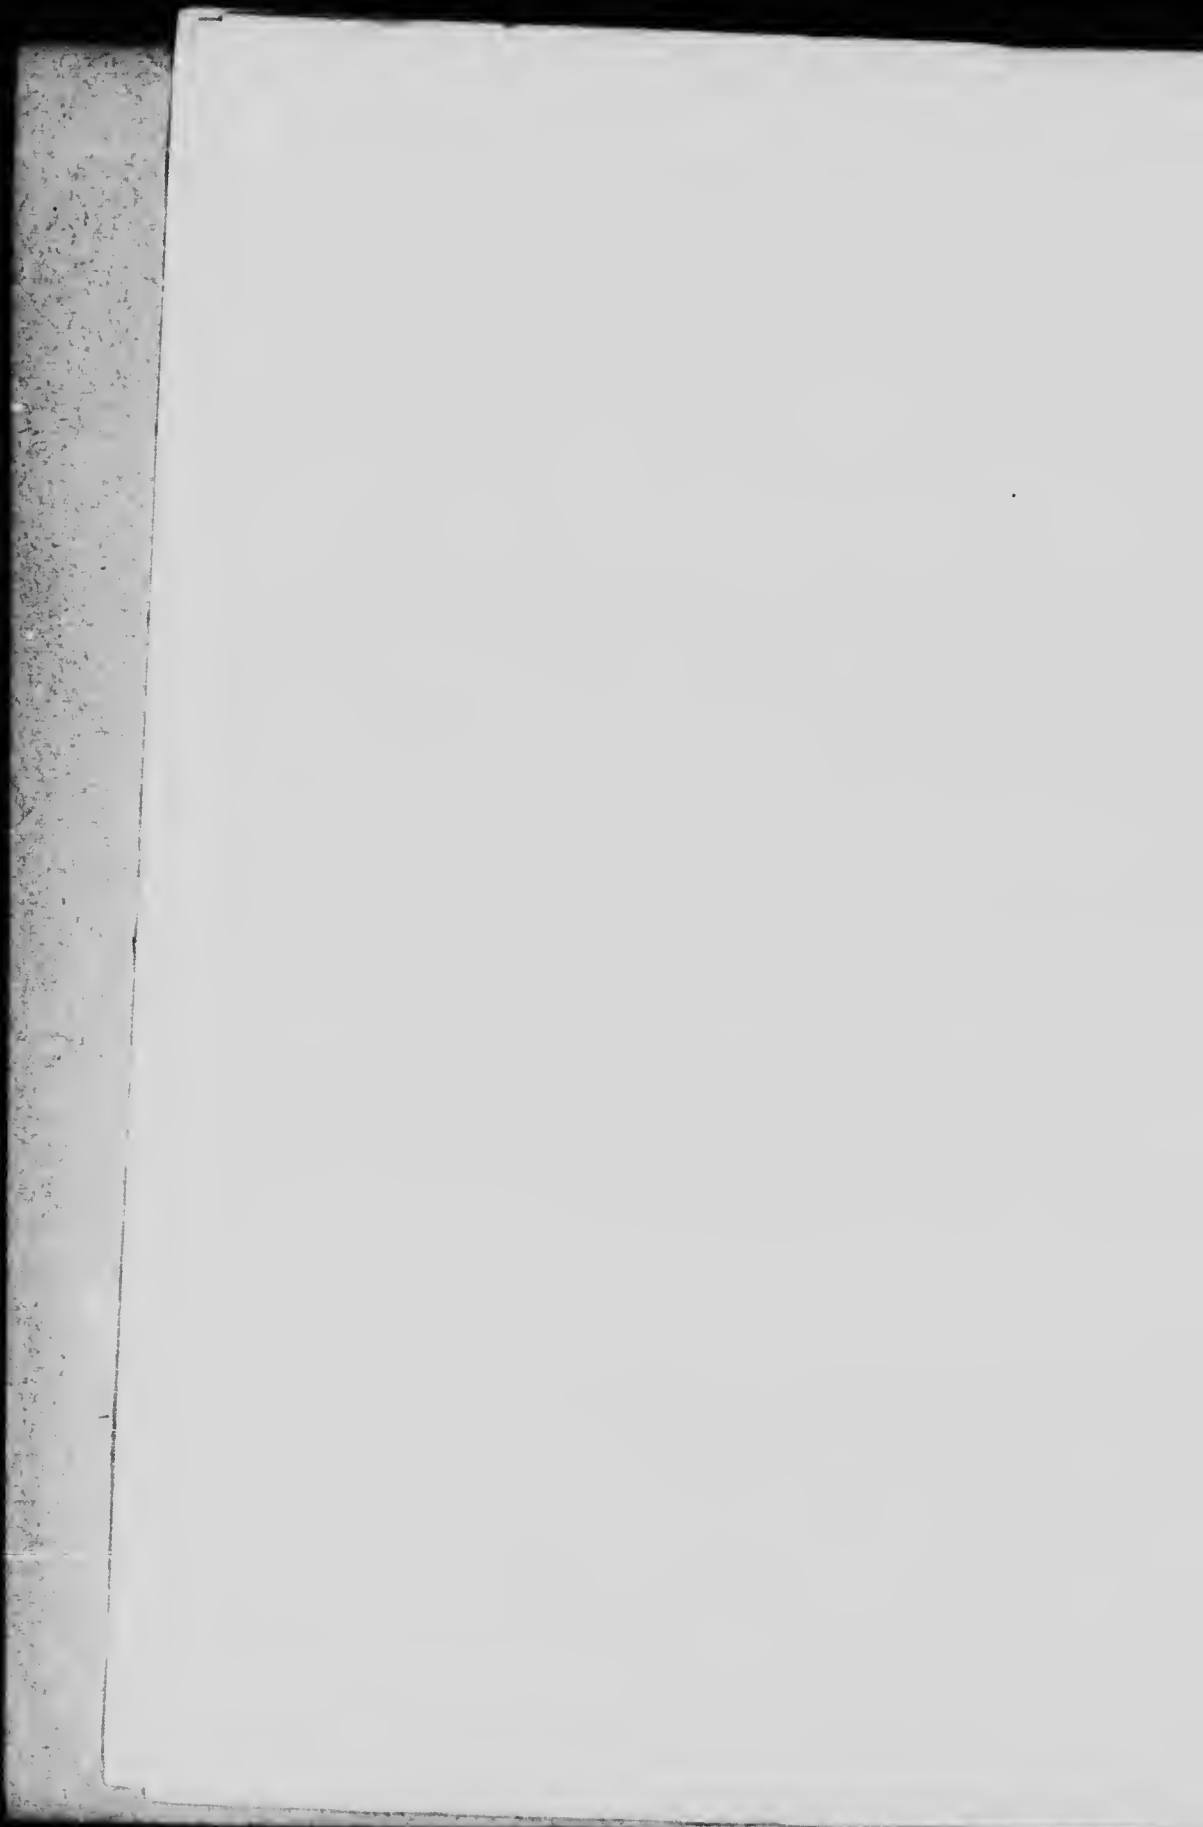


PLATE I.

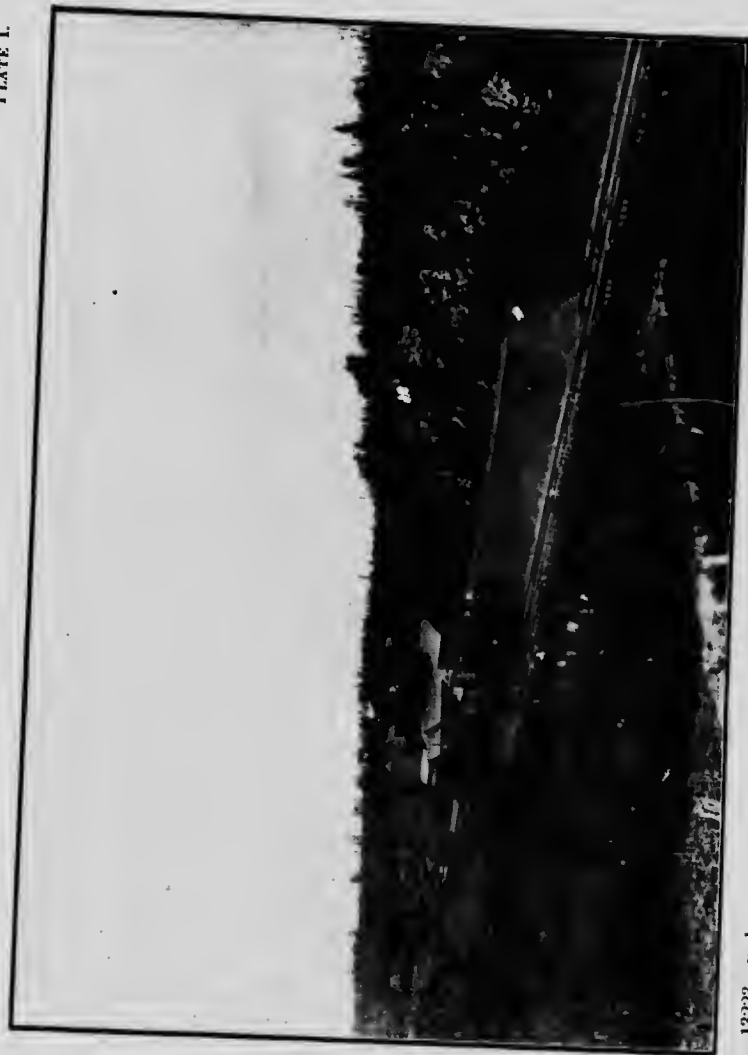

13223—p. 1

Austin Brook mining camp, N. B.

THE AUSTIN BROOK IRON-BEARING DISTRICT, NEW BRUNSWICK.

INTRODUCTORY.

Field work by the Mines Branch, in the Austin Brook iron-bearing district, New Brunswick, was commenced in the autumn of 1906, when a magnetometric survey, covering an area of about one square mile, was made by the writer. This survey led to the discovery of several ore deposits not previously known. During the months of June and July, 1910, this survey was extended by the writer, with the assistance of Mr. W. M. Morrison.

The total area covered by the two seasons' field-work is about 2 square miles. Inasmuch as a preliminary report, and magnetometric map covering the area surveyed in 1906, have already been issued by the Mines Branch, the objective of the present report is to give, in more detail, the results obtained during the two field seasons indicated above. Two maps have been prepared to accompany the report: one shows the distribution of the isodynamic lines of the vertical magnetic intensity; while the other shows the geology of the area. The magnetic observations were taken with a Thalen-Tiberg magnetometer, the distance between the points of observation varying from 25 to 100 feet, depending on the local complication of the magnetic field. On the geological sheet, an attempt has been made to outline the various ore deposits, as indicated by the magnetometric survey; but since the greater part of the area occupied by the ore bodies is drift covered, it has been possible to verify their outline only in a few places, by the actual observation of outcrops and contacts. Hence they are not, as a rule, well defined.

LOCATION.

The iron ore deposits are situated in the county of Gloucester, about 23 miles southwest of the town of Bathurst, in the vicinity of Austin brook, a small tributary of the Nipisiguit river. The elevation of the district is about 350 to 500 feet above sea-level. Its main topographical feature is the Nipisiguit valley, with generally steep banks, rising to a height

of 100 to 140 feet above the river. Back from the river, the country becomes comparatively flat, with occasionally a few outstanding small hills, generally having a northerly and southerly trend. The greater part of the area is drift covered, or occupied by muskegs, and is thickly wooded with spruce, cedar, balsam, poplar, birch, and maple.

HISTORY.

The first discovery of ore was made in 1897, by Mr. Wm. Hussey of Bathurst. In 1902, this gentleman—together with Mr. T. Burns of Bathurst—secured "Rights to Search" upon several 5 mile locations in the district. During 1903, representatives of the Dominion Iron and Steel Co. visited the property, and some trenching and test-pitting were done. In the autumn of 1906, at the request of O. Turgeon, M.P., the writer was instructed by the Director of the Mines Branch to make a magnetometric survey of the district. The result of this survey showed that the field contains a number of magnetic iron ore deposits, some of which are of large extent. In order to fully ascertain the quality of these ore bodies, the Provincial Government of New Brunswick was petitioned for the use of the diamond drill belonging to the Province. The petition was granted, and during the year 1907 seven drill-holes were put down. The records of five of these holes are given in the following pages. In November of 1907, the Austin Brook property passed into the control of the Canada Iron Corporation, Limited. A branch line, connecting the property with the Interecolonial railway at Blacks Cut, about 4 miles south of Bathurst, has been built, the distance from the mine to Blacks Cut being about 17 miles.

An ore dock for the transshipment of the ore has been completed by the Company at Newcastle. It consists of a 13,000 ton ore pocket. The ore is delivered from the pocket through a series of chutes into a horizontal bucket conveyer, operated on a track. This conveyer delivers the ore into an outer 150 ton pocket, situated on a dock. From this pocket the ore is loaded into the vessel by means of a self-feeding chute. The ore dock has a storage capacity of 13,000 tons, and its loading capacity is 3,000 tons per hour. The railway haul from the mine to Newcastle is 57 miles. During the last two years the following shipments have been made :—

1910.....	5,336 short tons
1911.....	31,120 " "

GEOLOGY.

The greater part of the area under consideration is underlain by quartz porphyry, generally of schistose structure; owing to the intense folding and shearing to which it has been subjected. Its general strike is about north and south, with a steep dip towards the west. Associated with the porphyry are bands of chloritic and sericitic schists, which may be merely alteration phases of the porphyry. Generally, the porphyry shows distinct phenocrysts of feldspar and quartz, in a dense grey matrix.

In the southern and western part of the area eruptive rocks of basic character are found intruding into the porphyry. These rocks may be classed as gabbro or diabase. They are usually of a greenish grey colour, with a granular to fine texture. Other intrusions in the porphyry are numerous quartz veins. These are also very common in the ore, but are rarely seen in the gabbro. They vary in size from a fraction of an inch up to several inches in width.

Sedimentary rocks, consisting of black and grey slates, highly tilted, and conformable to the porphyry, outcrop on the banks of the Nipisiguit river at Great falls, about $1\frac{1}{2}$ miles below the mouth of Austin brook; but have, so far, not been observed within the area under consideration. Similar rocks are also exposed about one mile above Austin brook; and farther up the Nipisiguit river, at the Narrows, fragments of black slates were seen embedded in the porphyry. The porphyry seems, therefore, to be intrusive in this slate formation, the geological age of which is early Palæozoic, probably Ordovician.¹

CHARACTER OF ORE.

The ore of the district consists of a very fine-grained siliceous magnetite, mixed with a considerable amount of hematite. It is often found interbanded with jasper and a green slaty gangue material, which give the deposits a conspicuous bedded structure. Veins of quartz are also—as already mentioned—of common occurrence, and generally follow the bedding planes of the ore. The metallic iron content of the various layers varies, therefore, considerably, ranging from 59 down to 35 per cent: the average being about 43 to 47 per cent.

The average phosphorous content is about 0.8 per cent, with the sulphur ranging from 0.03 to 0.1 per cent; but locally

¹ See Summary Report of the Geological Survey for 1909, p. 218.

the sulphur content is much higher. This is especially the case near the contact of the ore with the country rock, where layers of iron pyrites, varying in thickness from a fraction of an inch up to several feet, often occur.

The following tables give a number of analyses representing average samples taken by the writer :—

TABLE No. 1.

No. of sample	Metallic iron %	Insoluble %	Phosphorus %	Sulphur %	Manganese %	Notes
1.	43.7	26.3	0.64	0.05	1.00	Average sample from deposit No. 1, about 230 feet south of its northerly end.
2.	42.5	34.6	1.20	0.03	Not determined.	Average sample from deposit No. 1, about 100 feet north of Nipisiguit river.
3.	46.0	21.6	1.21	0.05	Not determined.	Average sample from deposit No. 1. Group II.
4.	46.6	24.7	1.04	0.02	1.8	Average sample from the southerly end of deposit No. 2. Group II.
5.	43.4	25.2	0.82	0.02	Not determined.	Average sample from the northerly end of deposit No. 2. Group II.
6.	43.6	33.1	0.40	0.007	0.5	Average sample from deposit No. 4. Group II.
7.	44.5	28.5	0.83	0.03	Not determined.	Average sample from Group III.
8.	47.5	22.7	0.65	0.05	1.2	Average sample from Group III.

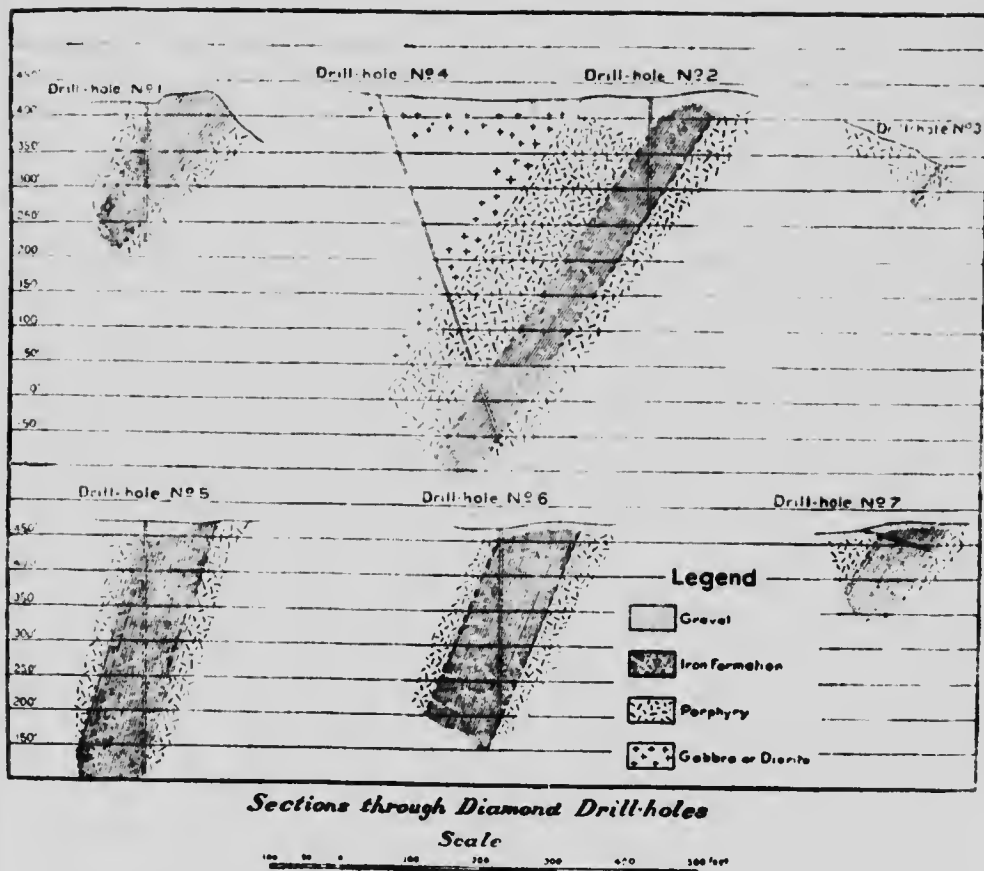


FIG. 1.

Table 2 gives the record of four drill holes. The cores were shipped to the laboratory of the Mines Branch, at Ottawa, and analysed there by Mr. H. A. Leverin. With few exceptions, the average length of core represented by each analysis is 10 feet. The core of hole No. 7 was analysed at the laboratory of the Canada Iron Corporation, and the results—kindly placed at the disposal of the writer by Mr. Fulton, superintendent of the mine—are given in Table 3.

TABLE No. 2.

Designation of drill hole.	Direction of drill hole.	Angle of drill hole.	Depth.	Analysis.				Remarks.
				Iron.	Insoluble.	Phosphorus.	Sulphur	
Drill hole No. 1.		90°	Feet. 0-35	%	%	%	%	
			35-40	48.0	17.5	0.95	0.11	Hanging wall, porphyry and schist. Iron formation.
			40-50	50.5	15.5	1.01	0.10	
			50-60	45.6	21.2	0.87	0.07	
			60-70	45.5	18.4	0.69	0.43	
			70-80	50.9	16.2	0.49	0.09	
			80-90	51.6	8.0	0.86	0.70	
			90-100	39.6	24.7	0.85	0.10	
			100-110	51.6	12.3	0.79	0.05	
			110-120	44.5	20.9	0.75	0.08	
			120-130	41.3	27.7	0.57	0.13	
			130-140	53.9	12.6	0.74	0.65	
			140-150	57.2	11.9	0.87	0.69	
			150-160	49.8	16.6	0.94	0.78	
			160-162	55.7	8.4	0.76	1.30	
			162-192					Footwall, porphyry and schist.
Drill hole No. 2.		90°	0-49					
			49-50	49.9	25.6	0.74	0.03	Gravel, etc. Iron formation
			50-60	58.1	17.1	0.55	0.15	
			60-70	58.7	13.3	0.70	0.03	
			70-72	49.7	23.6	0.91	0.17	
			72-82					Schist. Iron formation.
			82-90	44.5	12.4	0.83	0.27	
			90-100	51.7	19.0	0.60	0.27	
			100-110	50.1	19.6	0.88	0.04	
			110-120	48.3	16.0	0.72	0.19	
			120-130	50.1	16.4	0.71	0.10	
			130-140	52.0	14.6	0.97	0.68	
			140-150	45.1	10.1	1.08	18.21	
			150-160	35.0	15.2	0.53	32.97	
			160-162	44.1	6.9	0.50	37.08	
			162-172					Footwall, porphyry and schist.


TABLE No. 2—Continued.

Designation of drill hole.	Direction of drill hole.	Angle of drill hole.	Depth.	Analysis.				Remarks.
				Iron.	Insoluble.	Phosphorus.	Sulphur.	
Drill hole No. 4.	S. 80° E.	70°	Feet.					
			0- 8					
			8-434					Gravel.
								Hanging wall,
								gabbro, por-
								phyry, and
								quartz.
								Iron formation.
			434-444	44.2	28.0	0.38	0.04	
			444-454	42.5	24.0	0.73	0.09	
			454-464	48.5	17.3	0.98	0.03	
			464-474	45.4	16.1	1.00	0.06	
			474-484	46.7	16.2	1.08	0.08	
			484-494	50.8	14.8	0.87	0.15	
			494-504	50.1	15.3	1.13	0.75	
Drill hole No. 5.		90°	504-514				19.4	
			514-527				10.8	Footwall, por-
								phyry.
			0- 23					Pent and gra-
								vel.
								Iron formation.
			23- 32	50.5	17.8	0.90	0.09	
			32- 42	52.2	10.7	1.61	0.03	
			42- 52	52.1	13.8	1.03	0.04	
			52- 62	52.8	14.1	0.52	0.04	
			62- 72	55.8	10.5	0.90	0.04	
			72- 82	48.8	18.0	1.04	0.06	
			82- 92	50.2	18.0	0.96	0.06	
			92-102	41.7	22.5	0.37	0.04	
			102-112	43.0	20.5	0.81	0.04	
			112-122	39.5	23.1	1.22	0.03	
			122-132	51.1	15.0	0.98	0.04	
			132-142	54.1	15.0	0.53	0.06	
			142-152	42.7	17.6	0.90	0.35	
			152-162	41.7	18.5	0.64	0.12	
			162-172	45.1	18.0	0.88	0.07	
			172-182	47.0	17.5	1.18	0.11	
			182-192	47.9	16.8	0.73	1.38	
			192-202	38.2	21.8	0.96	1.49	
			202-212	47.9	12.6	0.62	0.90	
			212-222	51.6	13.8	0.91	0.14	
			222-232	49.5	16.6	0.96	2.43	
			232-242	53.5	13.4	0.81	0.08	
			242-252	56.5	12.6	0.67	0.08	
			252-262	55.3	7.9	0.70	0.13	
			262-272	48.5	15.3	1.09	0.13	
			272-282	42.6	19.1	0.71	0.09	
			282-292	48.0	17.3	0.81	0.03	
			292-302	45.6	21.4	0.78	0.07	
			302-312	51.5	13.7	0.98	0.05	
			312-322	52.3	13.0	1.07	0.03	
			322-332	54.9	13.3	0.93	0.06	
			332-342	50.7	14.6	0.78	0.37	
			342-347	59.5	6.5	0.72	0.20	
			347-353				18.2	

TABLE No. 2.

Designation of hole.	Direction of hole.	Angle of hole.	Depth of hole.	Metallic iron.	Insoluble.	Phosphorus.	Manganese.	Sulphur.	Alumina.	Lime.	Magnesia.	Remarks.
Drill hole. No. 7.	N. 75° E.	15°	Feet.	%	%	%	%	%	%	%	%	
			0-10									
			10-20									Gravel.
			20-40	36.3	25.0							Hanging wall,
			40-45	52.9	12.3							porphyry.
			45-50	55.1	17.3	0.81	1.0	0.10	1.0	1.3	0.7	Iron formation.
			50-55	53.8	19.7	0.40	0.8	0.07	0.4	1.5	0.5	
			55-61	51.3	18.8	0.50	1.1	0.37	0.3	1.3	0.6	
			61-62									No core.
			62-63	55.1	12.0							Iron formation.
			63-65									High in sulphur.
			65-71	52.5	19.2	0.81	1.2	0.11	0.1	1.9	0.4	Iron formation.
			71-78	52.7	17.5	0.73	1.2	0.10	0.1	1.8	0.4	
			78-83	53.5	15.9	0.71	2.0	0.13	0.2	1.7	0.3	
			83-86	28.6	39.9							
			86-92	48.2	17.7							
			92-99	55.6	13.0							
			99-106	54.2	14.1							
			106-109	46.0	23.5							
			109-129									Porphyry and iron pyrites.

PLATE II.

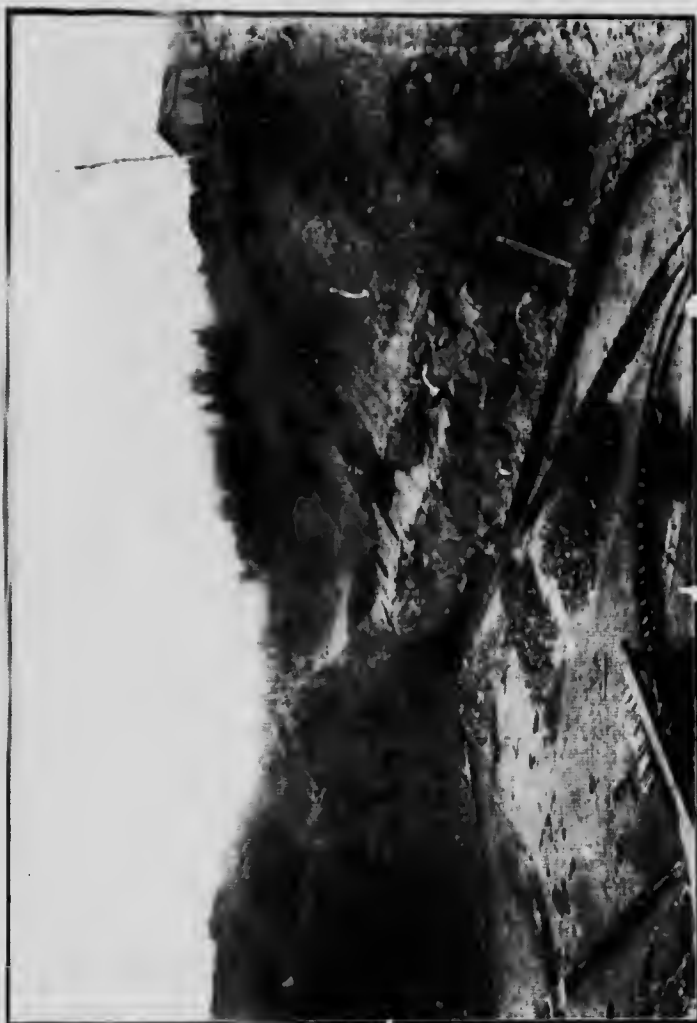

Open-cut on No. 1 deposit, Austin Brook, N. B.

13223 p. 8

DISTRIBUTION OF ORE BODIES.

As far as present knowledge goes, the ore occurs as elongated lenses in the quartz porphyry, and shows, in common with this, a prominent parting of schistosity, the plane of schistosity being parallel to that of the country rock. The ore bodies lie in three main groups, which for reference have been numbered I, II, and III.

Group I is situated west of Austin brook, and consists of one ore body, the total length of which is about 2,150 feet. The northern end of this deposit is well exposed, rising abruptly to a height of 75 feet above Austin brook. Farther south it is covered by gravel of considerable depth, but outcrops again about 100 feet from the Nipisiguit river, where its contact with the schistose porphyry is well exposed. The horizontal width of the ore body is, where drill hole No. 1 was sunk, 106 feet. This hole was put down vertically on the hanging wall about 250 feet south of the northern end of the deposit. It struck the ore body at a depth of 35 feet, and continued in the iron-bearing formation to 162 feet, when the foot-wall was reached, giving a calculated thickness to the ore body of about 85 feet. Drill hole No. 2 was sunk vertically, about 700 feet south of No. 1. After going through gravel, etc., it struck the ore body at a depth of 49 feet, and reached the foot-wall at 162 feet, giving a calculated thickness to the iron-bearing formation of about 60 feet. Drill hole No. 3 was located on the hanging wall of the deposit, about 150 feet from Nipisiguit river, and drilled vertically to a depth of 49 feet, giving a calculated width to the iron-bearing formation of about 8 feet. Drill hole No. 4 was sunk 380 feet west of No. 2, at an angle of 70° , the bearing of the hole being S. 80° E.

The total depth attained by the hole was 527 feet. It struck the iron-bearing formation at a depth of 434 feet, and continued in it to 514 feet, when the foot-wall was reached, giving a calculated thickness to the iron-bearing formation of about 64 feet.

Group II lies east of Austin brook, and is made up of several ore lenses, which for reference have been numbered 1, 2, 3, and 4.

No. 1 deposit outcrops on the hillslope towards the Nipisiguit river, but is, according to the magnetic survey, of inconsiderable extent. No. 2 deposit outcrops on the eastern bank of Austin brook. The southern end of the deposit is well exposed, showing a width of 42 feet, with well defined walls.

Farther north the deposit is covered by gravel, and few outcrops are available ; but judging from the magnetic survey, we may assume the length of the deposit to be about 250 feet. At the north end, its width is about 19 feet. No. 3 deposit lies in a gully about 180 feet north of No. 2, and is completely concealed by humus, except along the east bank, where its contact with the porphyry is exposed in a few places. The total length of the ore body is estimated at about 350 feet. No. 4 deposit is located east of No. 3. It has a length of about 400 feet. At the southern end of the deposit the width was proved by stripping to be 30 feet, but is decreasing towards the north.

North of groups I and II, there is no indication of iron ore for a distance of about 1,600 feet, then group III is encountered. This is for the most part covered by swamp, and it is only at its southern end that a few outcrops of ore can be seen. According to the result of the magnetometric survey, this iron-bearing area extends in a northerly direction for about 4,400 feet. It does not, however, consist of one continuous ore body, but is made up of a great number of ore lenses, which vary considerably in size. On the main deposit, which lies in the southern half of the area, drill holes No. 5 and No. 6 have been sunk vertically. In No. 5 ore was encountered at a depth of 23 feet, and the core was continuously in ore to 347 feet. Drill hole No. 6 was sunk to a depth of 276 feet, showing, however, very lean ore, thickly streaked with jasper. The average width of the deposit at the surface is about 100 feet, and its total length according to the magnetometric survey may approximately be estimated at about 830 feet. About 150 feet north of this deposit another ore lens is situated, on which drill hole No. 7 was sunk. This ore body has a total length of about 400 feet, with a maximum width at the surface of about 90 feet. Besides these two ore bodies the magnetometric survey indicates the presence of a number of others which are all covered by humus, and on which no diamond drilling, so far, has been done.

EXTENT OF ORE BODIES.

So far, the development work done on the deposits has been very slight, hence the data for estimating the ore tonnage is only meagre ; nevertheless an attempt has been made to calculate the probable area occupied by the ore bodies. As this estimate largely depends on the evidence furnished by the few diamond drill holes put down, and the magnetometric survey, it does not pretend to be anything but a very rough approximation.

PLATE III.



Concentrating mill at Austin Brook, N. B.

13223 p. 11.

The probable ore areas are as follows :—

Group I.....	122,000	sq. feet.
Group II.....	17,000	“ “
Group III.....	175,000	“ “
Total.....	314,000	“ “

MINING OPERATIONS.

From what has been said in regard to the extent of the various ore deposits, it is evident that a large quantity of ore is available in this district, which can be mined under very favourable conditions. The principal difficulty to be overcome, however, is to get a concentration process adaptable to the ore, a large percentage of which—as the foregoing analyses indicate—is, in its natural state, of too low grade to be marketable.

After some experimenting the operating concern has adopted a jigging process, and a mill has been erected to treat 70 tons of crude ore per hour. This has lately been described by Messrs. W. F. C. Parsons and E. M. Archibald, engineers of the Canada Iron Corporation—in the Canadian Mining Journal, from which the following particulars are taken:—

“The present mining operations are confined to No. 1 deposit, which, rising about 75 feet above Austin brook, is being worked as an open quarry with a face of about 60 feet. The ore is loaded by a steam shovel into 2½ ton cars, and trammed a short distance to the foot of an inclined trestle. On this trestle an up-and-down car haul is operated, consisting of two endless chains. The loaded cars conveyed to the top of the trestle deliver the ore through a revolving tippie into a hopper, from which it passes directly to a No. 8 K Gates crusher, where it is crushed to pass a 3½ inch ring, and then delivered on to a 24 inch belt conveyor discharging into the boot of a steel bucket elevator, which elevates it to the top of another building, where it is discharged on a small grizzly in order to remove the fines. Thence the ore passes through a revolving screen 4 feet in diameter and 6 feet long with 2 inch round holes. The under-size from this goes directly to a conveyor belt discharging into a large storage bin. The oversize passes into a set of Taylors

rolls 54 inch diameter and 24 inch face. The opening between the rolls is 1 inch. The product from the rolls is elevated by a steel bucket elevator to a second screen 4 feet in diameter, 6 feet long, and with 2 inch holes, from which any oversize is returned directly to the rolls. The undersize going to an 18 inch conveyor belt, which discharges into the storage bin. From the storage bin the ore is discharged through a revolving drum feeder into a 70 feet high bucket elevator, which in turn carries it to the top of the concentrating mill. The course of the ore in the concentrating mill is best shown by the accompanying flow sheet. The ore having been discharged from the bucket elevator is flushed into a series of revolving screens by a heavy stream of water and classified into five sizes—oversize of $1\frac{1}{4}$, $\frac{3}{4}$, $\frac{1}{2}$, $\frac{1}{4}$, and undersize of $\frac{1}{8}$ inch. The oversize from the $1\frac{1}{4}$ and $\frac{3}{4}$ inch screens goes to three 900-B jigs. The concentrates produced by the three jigs are discharged on to a conveyor belt and conveyed to the loading bin. The tailings are run through a set of Taylors rolls (26), 42 inch diameter, 16 inch face, having an opening between the rolls of $\frac{3}{8}$ inch, thence elevated by a bucket elevator to the third revolving screen (14), where it joins with the original feed, which passed through the two first trommels. The oversize from the $\frac{1}{2}$ inch trommel passes to 900-B jig (22, 23). The concentrate is discharged to the conveying belt for removal to the loading bin, and the tailings re-treated on one compartment (24) of No. 5 900-B jig.

The oversize of the $\frac{1}{4}$ inch screen goes to the second compartment (25) of No. 5 900-B jig, the tailings from which are re-treated on a 3 compartment jig (28). The undersize from the $\frac{1}{4}$ screen is treated on 29 and 30, both 4 compartment Hartz jigs. The hutch product and concentrates of the last compartments of these jigs are considered as middlings and are flushed back to the bucket elevator, and, returning through the $\frac{1}{2}$ inch trommel, are treated for a second time. The average iron content of the ore from the mine is given by the officials to be about 45 per cent. In order to overcome to some extent the high loss of iron in the tailings some slight rearrangement of the flow sheet has lately been made by which (28) the three compartment Hartz jig becomes a primary jig and (24-25) become a secondary jig, the concentrates from which are run to a separate stockpile, with an average iron content of about 46 per cent. The water consumption of the mill is about 2000 gallons per minute. The water is used over and over again and only about 500 gallons of fresh water per minute are added to maintain a certain degree of purity. The fresh water is pumped to the

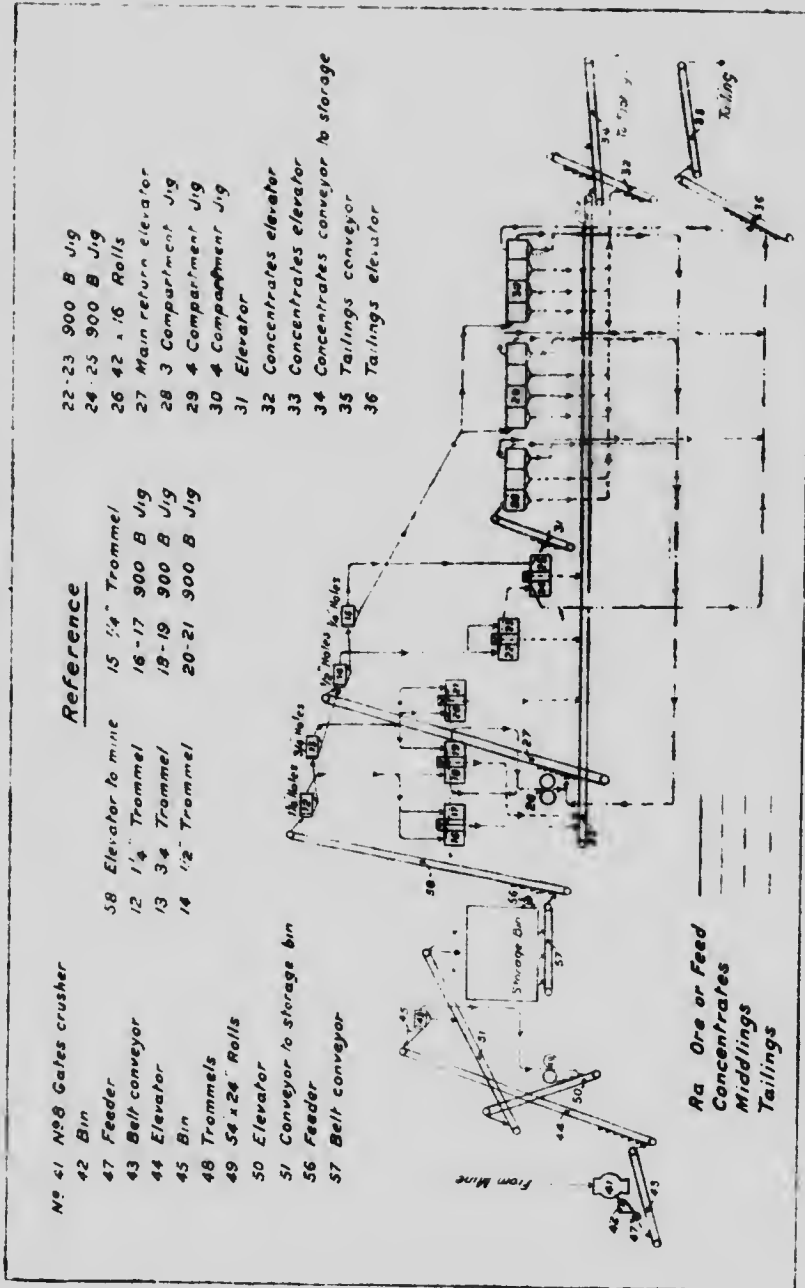


FIG. 2. Flow sheet of concentrating plant at Austin Brook. The Canada Iron Corporation, Limited.

top of the mill into the trommel house by a Knowles $12 \times 12 \times 10$ inch duplex steam pump, while the circulating water is being handled by an 8 inch single stage American Wellworks centrifugal pump, the circulating water being elevated from the settling tanks in the basement to a large launder located just above the highest jig level.


The 900-B jig is 14 feet long, 14 feet wide, and 10 feet high, with two separate jiggling compartments, and a centre compartment, containing an elevator which recovers the concentrates produced, elevates and discharges them to the belt conveyor. The sieve is 60×60 inches, supported on grate bars, and supports a bed of ore, ranging from 6 inches to 12 inches, depending on the size of material being jigged. The plunger is of a heavy cast iron construction, 54 inches in diameter, working in a heavy iron cylinder with four inlet water valves 8×10 inches. An adjustable eccentric provides for a variation in the length of the stroke. A 4 inch stroke at 100 r. p. m. is necessary to properly stratify a bed of 2 inch ore. The plunger shaft is fitted with tight and loose pulleys to enable the jig to be put out of commission without affecting other jigs. A worm conveyor carries the hutch product, or what passes through the holes in the bed screens, to the centre compartment, where it is delivered to the concentrates elevator. The heavier material on the jig bed rapidly works its way to the bottom and is drawn off at the front of the jig through a draw-off valve, 48 inches long, while the lighter material passes over an apron on the top of the bed. The draw-off valve is capable of wide adjustment. The concentrates after passing the draw-off valve fall down a 45° slope to the elevator boot in the centre compartment.

The three compartment Hartz jig has a sieve bed 30×42 inches and runs at 125 r. p. m.

The four compartment Hartz has a sieve bed of 32×42 inches and runs at 180 r. p. m. and the concentrates are drawn off at the bottom of each bed by an adjustable draw-off valve.

The power plant of the mine consists of five tubular boilers rated at 125 H.P. each, one Inglis Corliss compound $16 \times 32 \times 36$ inches steam engine, which operates the bank-head apparatus and crushing machinery, one 18×20 inch Robb Corliss engine operating the mill, and one Allis-Chalmers air compressor with a capacity of 1290 cubic feet per minute of free air at 120 r. p. m."



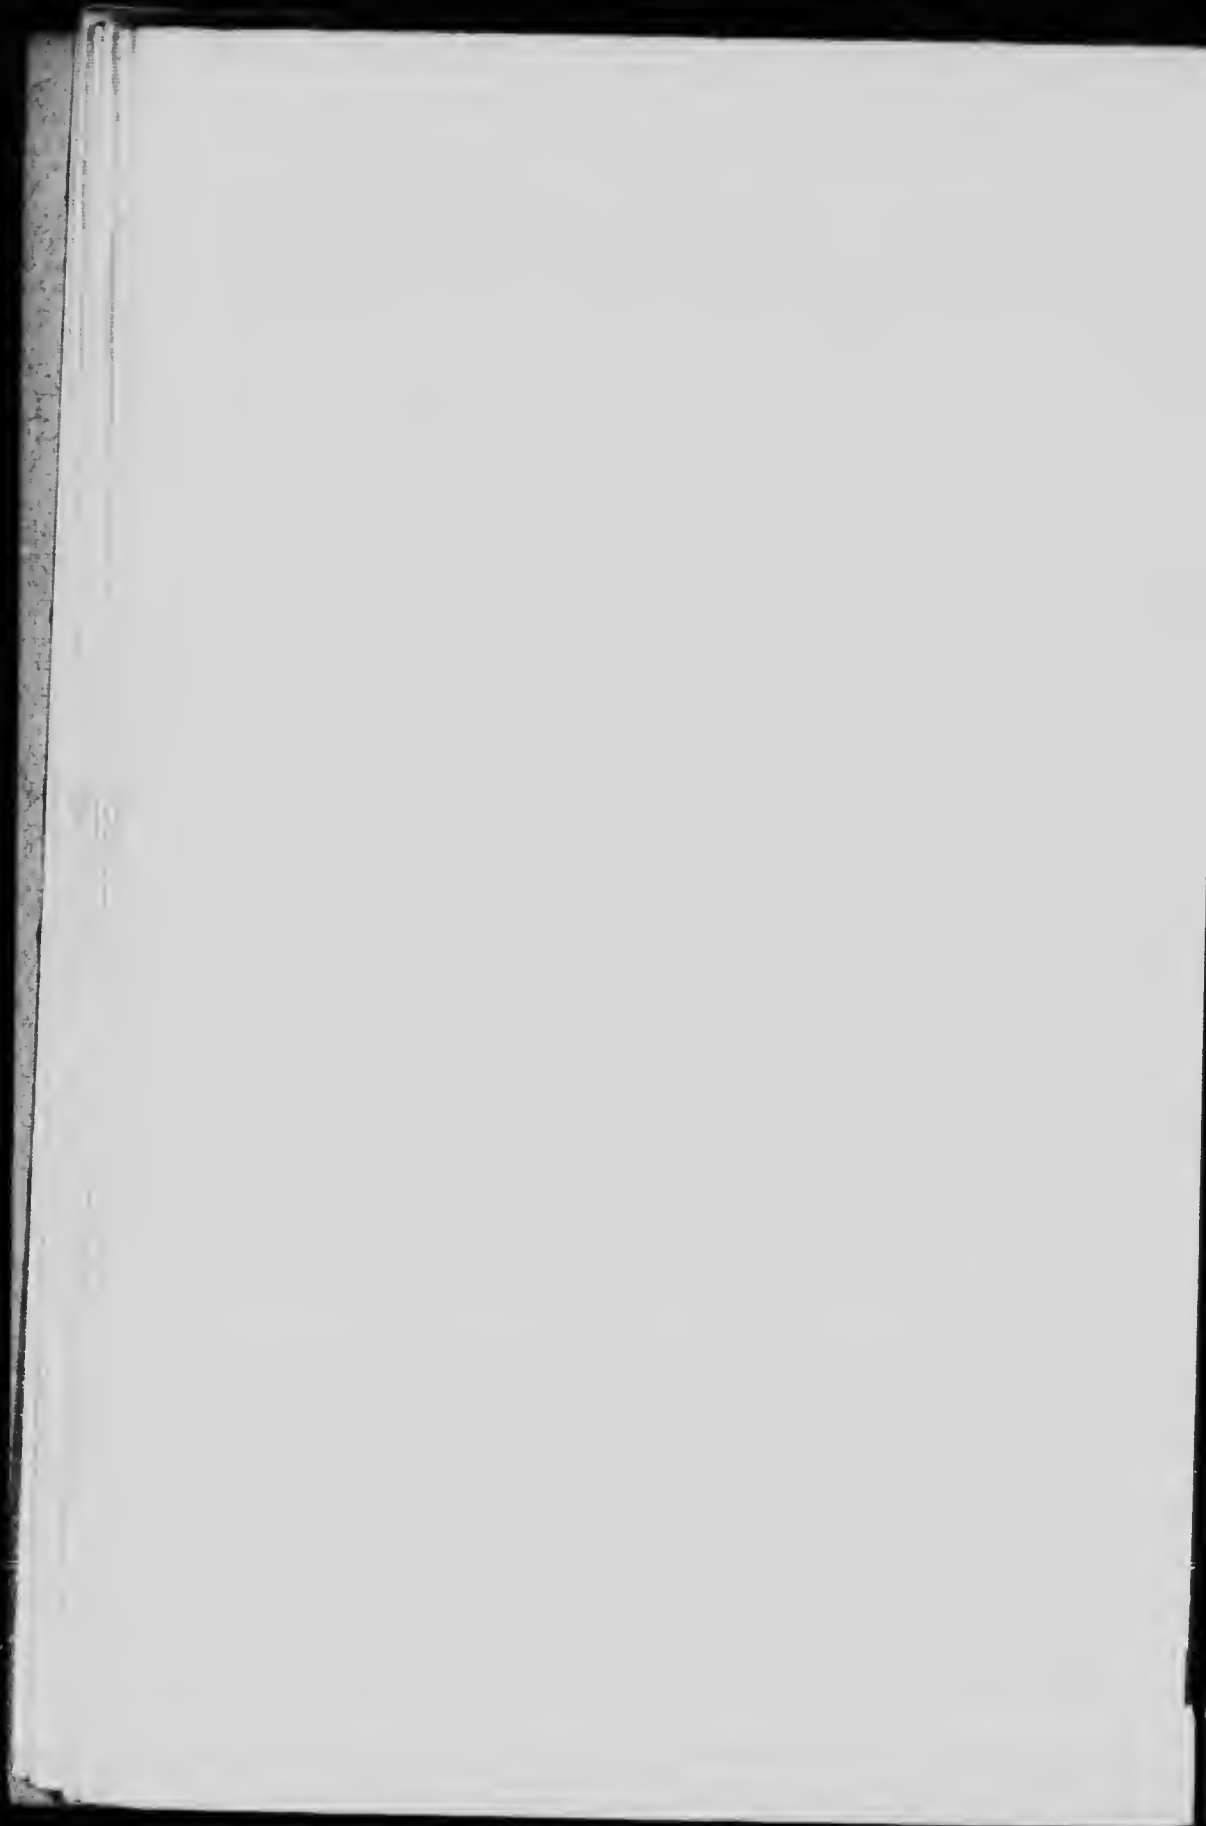

...
be
of,
ar
of,
—
is,
V.
ry
at:
ce
ort
an
of
it.
of
8.


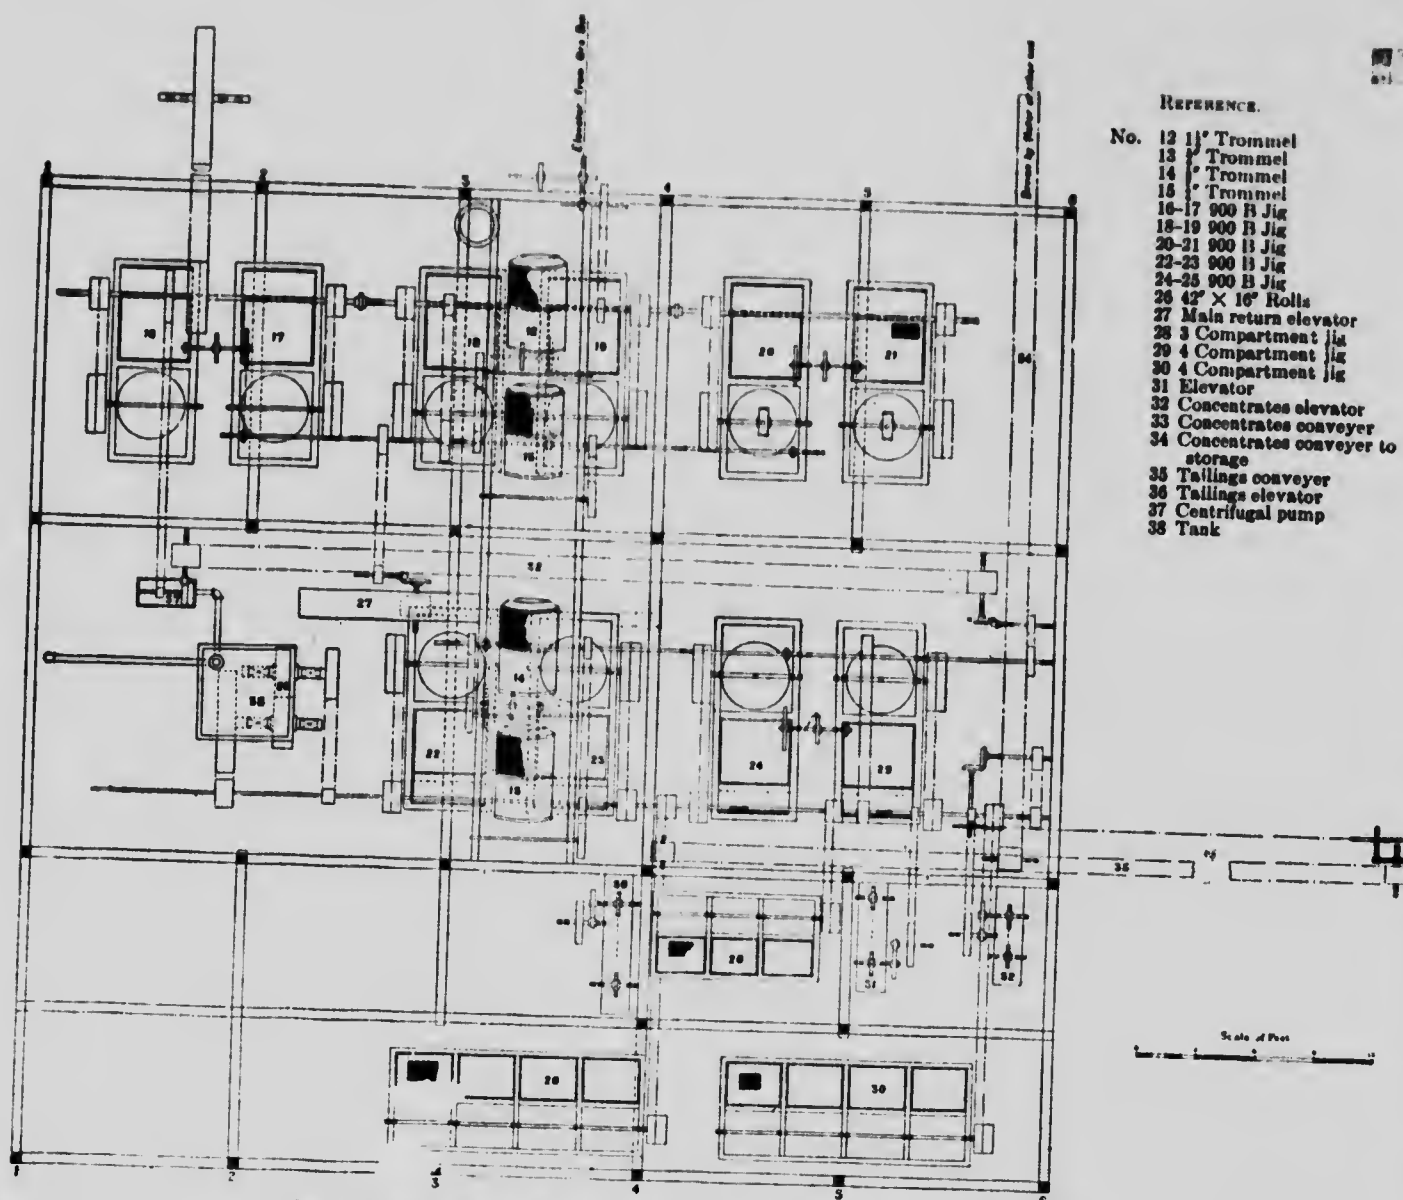


FIG. 4. Plan of concentrating mill at Austin Brook. The Canada Iron Corporation, Limited.




- LEGEND.
- No. 56 Feeder
 57 Belt conveyer
 58 Elevator to mill
 12 1 1/2' Trommel
 13 3' Trommel
 14 4' Trommel
 15 4' Trommel
 18-19 900 B Jig
 22-23 900 B Jig
 29 4 Compartment jig
 33 Concentrates conveyer
 36 Tailings elevator

Scale of Feet

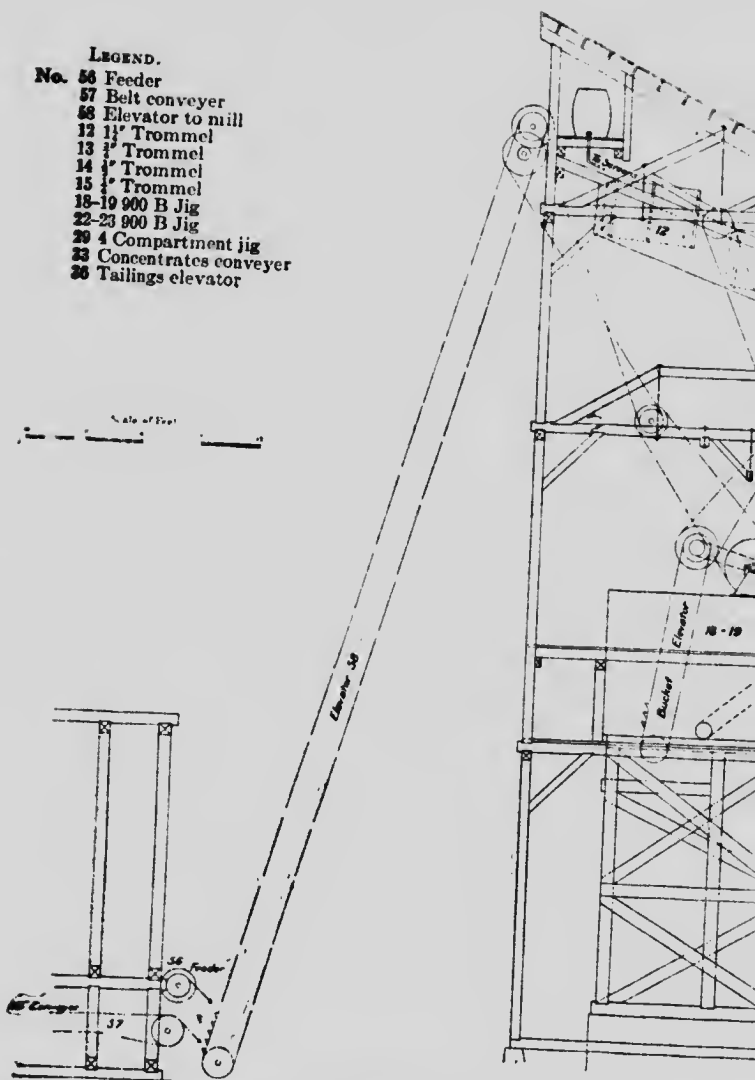


13223—p. 17.

FIG. 5. Section between 3 and 4 (Fig. 4) of concentrating plant

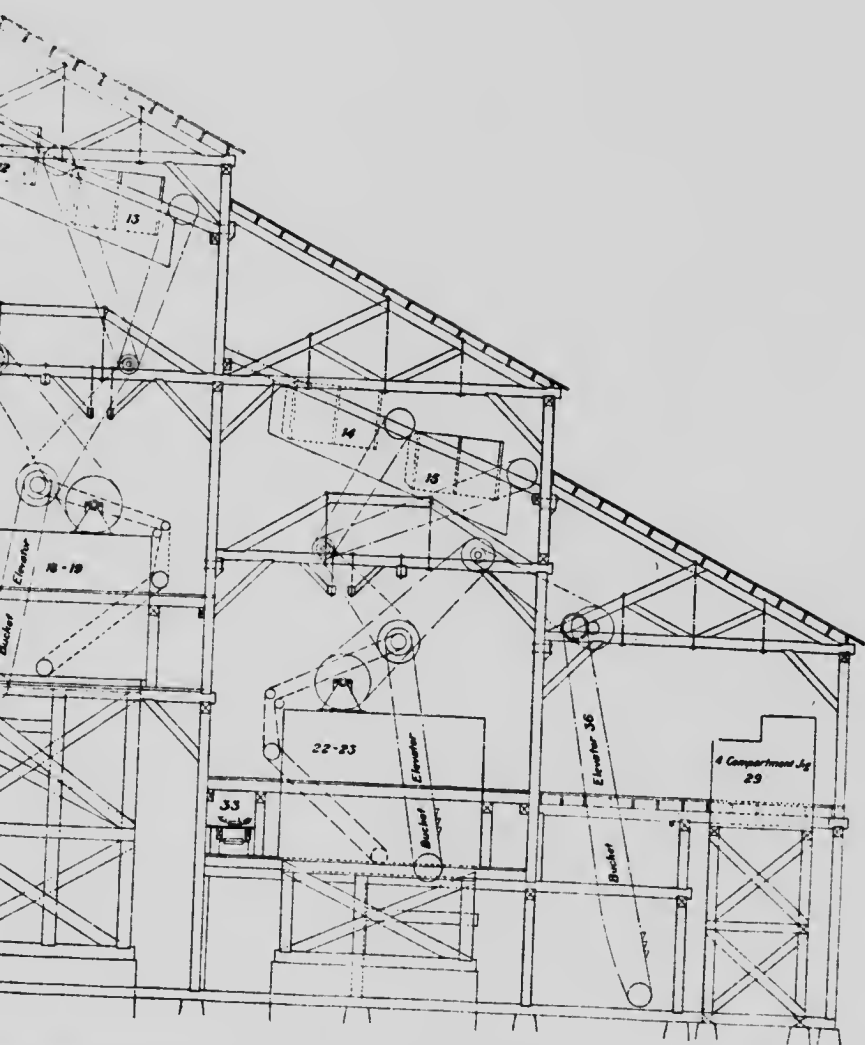

Processing plant at Austin Brook. The Canada Iron Corporation, Limited.

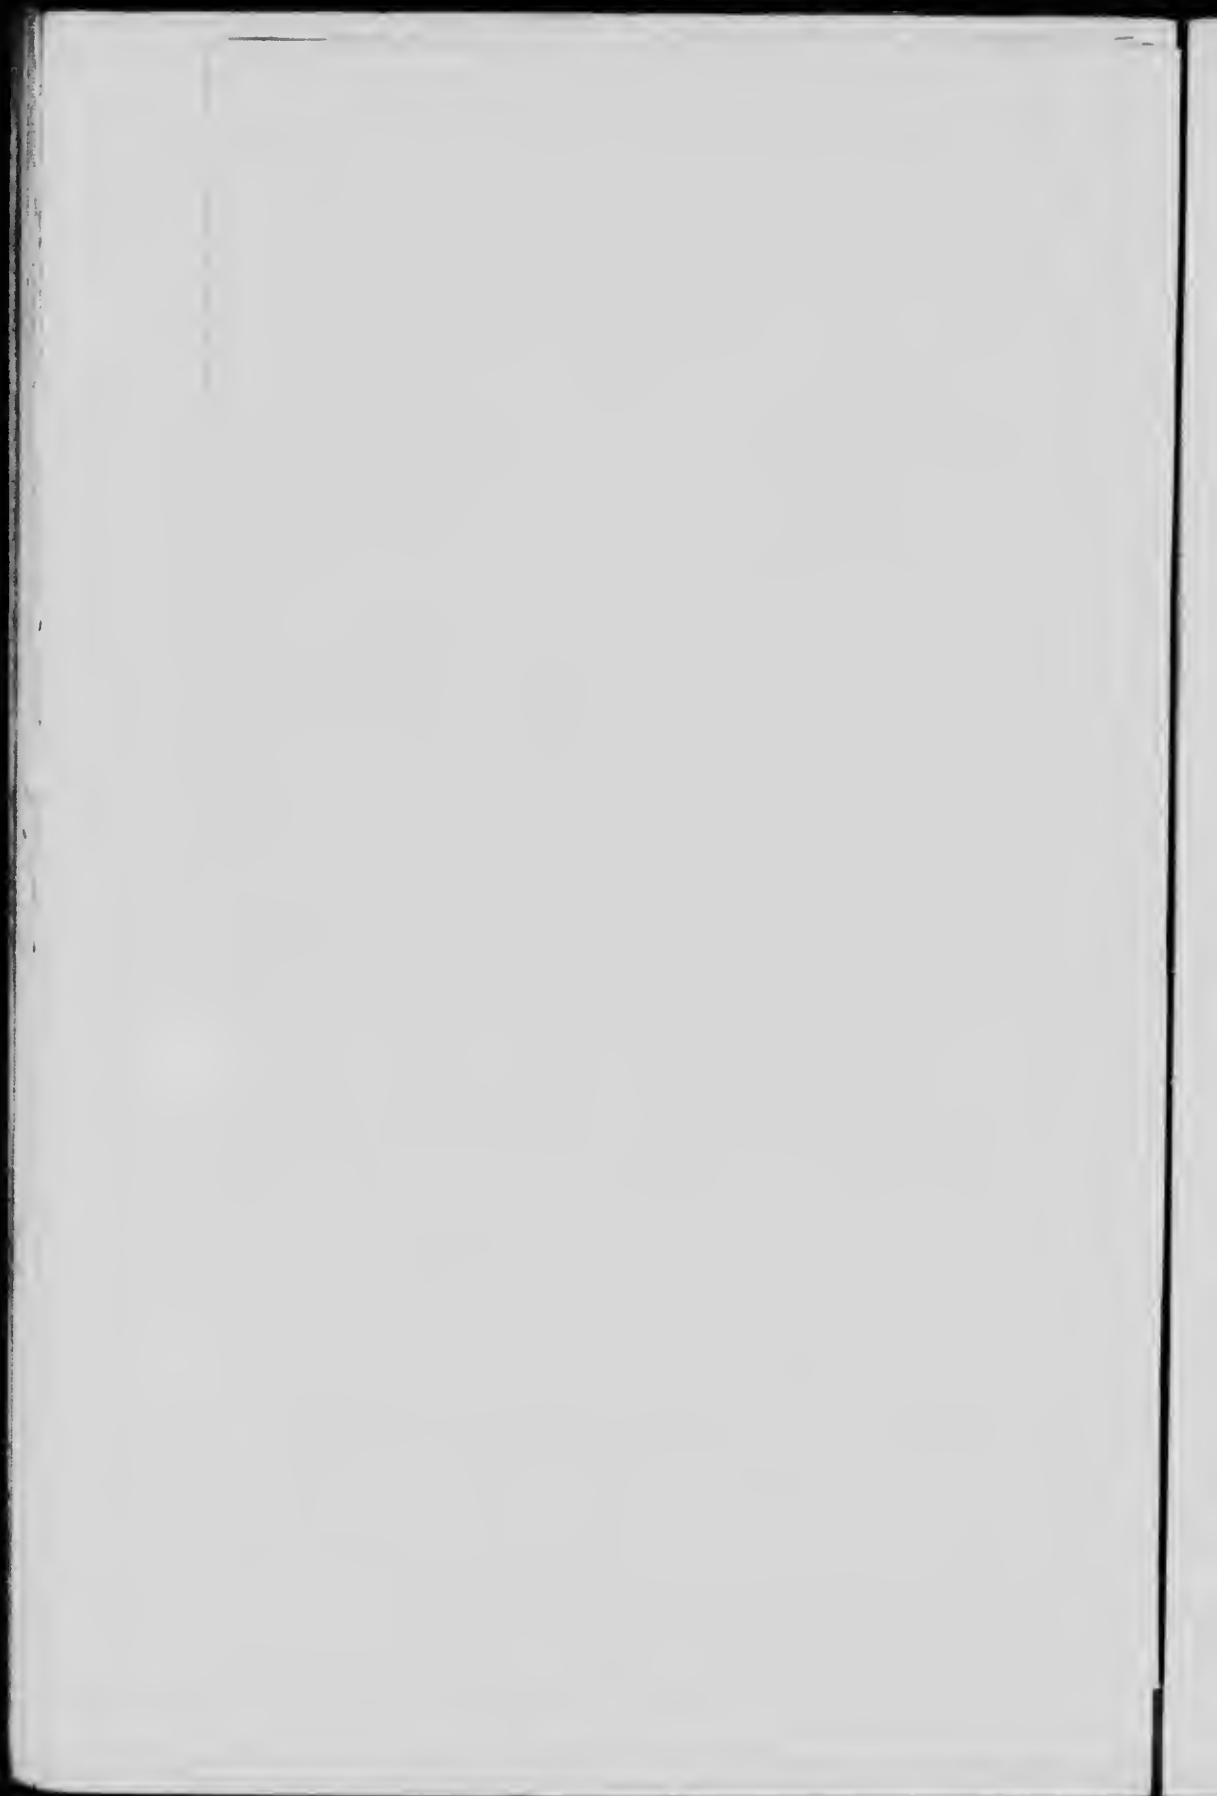

CANADA
DEPARTMENT OF MINES

HON. LOUIS CODERRE, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;

MINES BRANCH

EUGENE HAANEL, Ph.D., DIRECTOR.

REPORTS AND MAPS OF ECONOMIC INTEREST

PUBLISHED BY THE
MINES BRANCH

REPORTS.

1. Mining Conditions in the Klondike, Yukon. Report on—by Eugene Haanel, Ph.D., 1902.
2. Great Landslide at Frank, Alta. Report on—by R. G. McConnell and R. C. Brock, M.A., 1903. (Out of print.)
3. Investigation of the different electro-thermic processes for the smelting of iron ores, and the making of steel, in operation in Europe. Report of Special Commission—by Dr. Haanel, 1904. (Out of print.)
4. Rapport de la Commission nommée pour étudier les divers procédés électro-thermiques pour la réduction des minerais de fer et la fabrication de l'acier employées en Europe—by Dr. Haanel, (French Edition), 1905. (Out of print.)
5. On the location and examination of magnetic ore deposits by magnetometric measurements—by Dr. Haanel, 1904.
7. Limestones, and the Lime Industry of Manitoba. Preliminary Report on—by J. W. Wells, 1905. (Out of print.)
8. Clay and Shales of Manitoba: Their Industrial Value. Preliminary Report on—by J. W. Wells, 1905. (Out of print.)
9. Hydraulic Cements (Raw Materials) in Manitoba: Manufacture and Uses of. Preliminary Report on—by J. W. Wells, 1905. (Out of print.)
10. Mica: Its Occurrence, Exploitation, and Uses—by Fritz Cirkel, M.E., 1905. (Out of print: see No. 118.)
11. Asbestos: Its Occurrence, Exploitation, and Uses—by Fritz Cirkel, 1905. (Out of print: see No. 69.)
12. Zinc Resources of British Columbia and the Conditions affecting their Exploitation. Report of the Commission appointed to investigate—by W. R. Ingalls, 1905. (Out of print.)
16. Experiments made at Sault Ste. Marie, under Government auspices, in the smelting of Canadian iron ores by the electro-thermic process. Final Report on—by Dr. Haanel, 1907. (Out of print.)
17. Mines of the Silver-Cobalt Ores of the Cobalt district: Their Present and Prospective Output. Report on—by Dr. Haanel, 1907. (Out of print.)
18. Graphite: Its Properties, Occurrence, Refining, and Uses—by Fritz Cirkel, 1907. (Out of print.)
19. Peat and Lignite: Their Manufacture and Uses in Europe—by Erik Nystrom, M.E., 1908. (Out of print.)
20. Iron Ore Deposits of Nova Scotia. Report on (Part 1)—by Dr. J. E. Woodman.

*A few copies of the Preliminary Report, 1906, are still available.

21. Summary Report of Mines Branch, 1907-8. (Out of print.)
22. Iron Ore Deposits of Thunder Bay and Rainy River districts. Report on—by F. Hille, M.E.
23. Iron Ore Deposits, along the Ottawa (Quebec side) and Gatineau rivers. Report on—by Fritz Cirkel. (Out of print.)
24. General Report on the Mining and Metallurgical Industries of Canada, 1907-8.
25. The Tungsten Ores of Canada. Report on—by Dr. T. L. Walker.
26. The Mineral Production of Canada, 1906. Annual Report on—by John McLeish, B.A.
- 26a. French translation: The Mineral Production of Canada, 1906. Annual Report on—by John McLeish.
27. The Mineral Production of Canada, 1907. Preliminary Report on—by John McLeish.
- 27a. The Mineral Production of Canada, 1908. Preliminary Report on—by John McLeish. (Out of print.)
28. Summary Report of Mines Branch, 1908. (Out of print.)
- 28a. French translation: Summary Report of Mines Branch, 1908. (Out of print.)
29. Chrome Iron Ore Deposits of the Eastern Townships. Monograph on—by Fritz Cirkel. (Supplementary Section: Experiments with Chromite at McGill University—by Dr. J. B. Porter).
30. Investigation of the Peat Bogs and Peat Fuel Industry of Canada, 1908. Bulletin No. 1—by Erik Nystrom, and A. Anrep, Peat Expert.
32. Investigation of Electric Shaft Furnace, Sweden. Report on—by Dr. Haanel.
47. Iron Ore Deposits of Vancouver and Texada islands. Report on—by Einar Lindeman, M.E.
55. Report on the Bituminous, or Oil-shales of New Brunswick and Nova Scotia; also on the Oil-shale Industry of Scotland—by Dr. R. W. Ellis.
58. The Mineral Production of Canada, 1907 and 1908. Annual Report on—by John McLeish.

Note.—The following preliminary Bulletins were published prior to the issuance of the Annual Report for 1907-8.

31. Production of Cement in Canada, 1908. (Out of print.)
42. Production of Iron and Steel in Canada during the Calendar Years 1907 and 1908.
43. Production of Chromite in Canada during the Calendar Years 1907 and 1908.
44. Production of Asbestos in Canada, during the Calendar Years 1907 and 1908.
45. Production of Coal, Coke, and Peat in Canada, during the Calendar Years 1907 and 1908. (Out of print.)
46. Production of Natural Gas and Petroleum in Canada during the Calendar Years 1907 and 1908.
59. Chemical Analyses of Special Economic Importance made in the Laboratories of the Department of Mines, 1906-7-8. Report on—by F. G. Wait, M.A., F.C.S. (With Appendix on the Commercial Methods and Apparatus for the Analysis of Oil-shales—by H. A. Leverin, Ch. E.).

Schedule of Charges for Chemical Analyses and Assays.

62. Mineral Production of Canada, 1909. Preliminary Report on—by John McLeish.
63. Summary Report of Mines Branch, 1909.
67. Iron Ore Deposits of the Bristol Mine, Pontiac County, Quebec. Bulletin No. 2—by Einar Lindeman and Geo. C. Mackenzie, B.Sc.
68. Recent Advances in the Construction of Electric Furnaces for the Production of Pig Iron, Steel, and Zinc. Bulletin No. 3—by Dr. Haanel. (Out of print.)

69. Chrysotile-Asbestos: Its Occurrence, Exploitation, Milling, and Uses. Report on—by Fritz Cirkel. (Second Edition, enlarged.)
71. Investigation of the Peat Bogs, and Peat Industry of Canada, 1909-10; to which is appended Mr. Alf. Larson's Paper on Dr. M. Ekenberg's Wet-Carbonizing Process: from Teknisk Tidskrift, No. 12, December 26, 1908—translation by Mr. A. Anrep, Jr.; also a translation of Lieut. E. Lebert's pamphlet entitled 'A Solution of the Peat Problem,' 1909, describing the Ekelund Process for the Manufacture of Peat Powder, by Harold A. Leverin, Ch.E. Bulletin No. 4—by A. Anrep (Second Edition, enlarged). (Out of print.)
81. French Translation: Chrysotile-Asbestos, Its Occurrence, Exploitation, Milling, and Uses. Report on—by Fritz Cirkel.
82. Magnetic Concentration Experiments. Bulletin No. 5—by Geo. C. Mackenzie.
83. An investigation of the Coals of Canada with reference to their Economic Qualities: as conducted at McGill University under the authority of the Dominion Government. Report on—by J. B. Porter, E.M., D.Sc., R. J. Durley, Ma.E., and others—
Vol. I—Coal Washing and Coking Tests.
Vol. II—Boiler and Gas Producer Tests.
Vol. III—
Appendix I
Coal Washing Tests and Diagrams.
Vol. IV—
Appendix II
Boiler Tests and Diagrams.
Vol. V—
Appendix III
Producer Tests and Diagrams.
Vol. VI—
Appendix IV
Coking Tests.
Appendix V
Chemical Tests.
84. Gypsum Deposits of the Maritime Provinces of Canada—including the Magdalen islands. Report on—by W. F. Jennison, M.E. (Out of print.)
88. The Mineral Production of Canada, 1909. Annual Report on—by John McLeish.

NOTE.—The following preliminary Bulletins were published prior to the issuance of the Annual Report for 1909.

 79. Production of Iron and Steel in Canada during the Calendar Year 1909. (Out of print.)
 80. Production of Coal and Coke in Canada during the Calendar Year 1909. (Out of print.)
 85. Production of Cement, Lime, Clay Products, Stone, and other Structural Materials during the Calendar Year 1909.
89. Reprint of Presidential address delivered before the American Peat Society of Ottawa, July 25, 1910. By Dr. Haanel.
90. Proceedings of Conference on Explosives.
92. Investigation of the Explosives Industry in the Dominion of Canada, 1910. Report on—by Capt. Arthur Desborough. (Second Edition.)
93. Molybdenum Ores of Canada. Report on—by Dr. T. L. Walker.
100. The Building and Ornamental Stones of Canada. Report on—by Professor W. A. Parks.
102. Mineral Production of Canada, 1910. Preliminary Report on—by John McLeish.
103. Summary Report of Mines Branch, 1910. (Out of print.)
104. Catalogue of Publications of Mines Branch, from 1902 to 1911; containing Tables of Contents and List of Maps, etc.
105. Austin Brook Iron-bearing district, New Brunswick. Report on—by Einar Lindeman.
110. Western Portion of Torbrook Iron Ore Deposits, Annapolis county, N.S. Bulletin No. 7—by Howells Fréchette, M.Sc.

- 111. Diamond Drilling at Point Mainaise, Ont. Bulletin No. 6—by A. C. Lane, Ph.D., with Introductory by A. W. G. Wilson, Ph.D.
- 118. Mica: Its Occurrence, Exploitation, and Uses. Report on—by Hugh S. de Schmid, M.E.
- 142. Summary Report of Mines Branch, 1911.
- 143. The Mineral Production of Canada, 1910. Annual Report on—by John McLeish.

NOTE.—The following preliminary Bulletins were published prior to the issuance of the Annual Report for 1910.

- 114. Production of Cement, Lime, Clay Products, Stone, and other Structural Materials in Canada, 1910. (Out of print.)
- 115. Production of Iron and Steel in Canada during the Calendar Year 1910. (Out of print.)
- 116. Production of Coal and Coke in Canada during the Calendar Year 1910. (Out of print.)
- 117. General Summary of the Mineral Production of Canada during the Calendar Year 1910. (Out of print.)
- 145. Magnetic Iron Sands of Natashkwan, Saguenay county, Que. Report on—by Geo. C. MacKenzie.
- 150. The Mineral Production of Canada, 1911. Preliminary Report on—by John McLeish. (Out of print.)
- 151. Investigation of the Peat Bogs and Peat Industry of Canada, 1910-11. Bulletin No. 8—by A. Anrep.
- 154. The Utilization of Peat Fuel for the Production of Power, being a record of experiments conducted at the Fuel Testing Station, Ottawa, 1910-11. Report on—by B. F. Haanel, B.Sc.
- 167. Pyrites in Canada: Its Occurrence, Exploitation, Dressing, and Uses. Report on—by A. W. G. Wilson.
- 170. The Nickel Industry: with Special Reference to the Sudbury region, Ont. Report on—by Prof. A. P. Coleman, Ph.D.
- 197. French translation: Molybdenum Ores of Canada. Report on—by Dr. T. L. Walker.
- 198. French translation: Peat and Lignite: Their Manufacture and Uses in Europe—by Erik Nystrom, M.E., 1908.
- 201. The Mineral Production of Canada during the Calendar Year 1911. Annual Report on—by John McLeish.

NOTE.—The following preliminary Bulletins were published prior to the issuance of the Annual Report for 1911.

- 181. Production of Cement, Lime, Clay Products, Stone, and other Structural Materials in Canada during the Calendar Year 1911. Bulletin on—by John McLeish.
- 182. Production of Iron and Steel in Canada during the Calendar Year 1911. Bulletin on—by John McLeish.
- 183. General Summary of the Mineral Production in Canada during the Calendar Year 1911. Bulletin on—by John McLeish.
- 199. Production of Copper, Gold, Lead, Nickel, Silver, Zinc, and other Metals of Canada, during the Calendar Year 1911. Bulletin on—by C. T. Cartwright.
- 200. The Production of Coal and Coke in Canada during the Calendar Year 1911. Bulletin on—by John McLeish.
- 202. French translation: Graphite: Its Properties, Occurrence, Refining, and Uses—by Fritz Cirkel, 1907.
- 216. The Mineral Production of Canada, 1912. Preliminary Report on—by John McLeish.

IN THE PRESS.

156. French translation: The Tungsten Ores of Canada. Report on—by Dr. T. L. Walker.
184. Magnetite Occurrences along the Central Ontario Railway. Report on—by P. Lindeman.
190. French translation: Investigation of the Peat Bogs and Peat Industry of Canada, 1909-10; to which is appended Mr. Alf. Larson's paper on Dr. Ekenburg's Wet-Carbonizing Process; from Teknisk Fidskrift, No. 12, December 26, 1908—translation by Mr. A. Anrep; also a translation of Lieut. Ekelund's Pamphlet entitled "A Solution of the Peat Problem," 1909, describing the Ekelund Process for the Manufacture of Peat Powder, by Harold A. Leverin, Ch.E. Bulletin No. 4—by A. Anrep. (Second Edition, enlarged.)
203. Building Stones of Canada—Vol. II. Building and Ornamental Stones of the Maritime Provinces. Report on—by W. A. Parks.
224. Summary Report of Mines Branch, 1912.
233. French translation: Gypsum Deposits of the Maritime Provinces of Canada—including the Magdalen Islands. Report on—by W. F. Kennison.

NOTE.—Lists of manufacturers of clay products, stone quarry operators, and operators of limekilns, are prepared annually by the Division of Mineral Resources and Statistics, and copies may be had on application.

MAPS.

- *6. Magnetometric Survey, Vertical Intensity: Calabogie Mine, Bagot township, Renfrew county, Ontario—by E. Nystrom, 1904.
- *13. Magnetometric Survey of the Belmont Iron Mines, Belmont township, Peterborough county, Ontario—by B. F. Hamel, 1905.
- *14. Magnetometric Survey of the Wilbur Mine, Lavant township, Lanark county, Ontario—by B. F. Hamel, 1905.
- *33. Magnetometric Survey, Vertical Intensity: Lot 1, Concession VI, Mayo township, Hastings county, Ontario—by Howells Fréchette, 1909.
- *34. Magnetometric Survey, Vertical Intensity: Lots 2 and 3, Concession VI, Mayo township, Hastings county, Ontario—by Howells Fréchette, 1909.
- *35. Magnetometric Survey, Vertical Intensity: Lots 10, 11, and 12, Concession IX, and Lots 11 and 12, Concession VIII, Mayo township, Hastings county, Ontario—by Howells Fréchette, 1909.
- *36. Survey of Mcr Bleue Peat Bog, Gloucester township, Carleton county, and Cumberland township, Russell county, Ontario—by Erik Nystrom, and A. Anrep.
- *37. Survey of Alfred Peat Bog, Alfred and Caledonia townships, Prescott county, Ontario—by Erik Nystrom, and A. Anrep.
- *38. Survey of Welland Peat Bog, Wainfleet and Humberstone townships, Welland county, Ontario—by Erik Nystrom and A. Anrep.
- *39. Survey of Newington Peat Bog, Osnabrook, Roxborough, and Cornwall townships, Stormont county, Ontario—by Erik Nystrom, and A. Anrep.
- *40. Survey of Perth Peat Bog, Drummond township, Lanark county, Ontario—by Erik Nystrom, and A. Anrep.
- *41. Survey of Victoria Road Peat Bog, Bexley and Carden townships, Victoria county, Ontario—by Erik Nystrom and A. Anrep.
48. Magnetometric Map of Iron Crown claim at Klabanch river, Vancouver island, B.C.—by Einar Lindeman.
49. Magnetometric Map of Western Steel Iron claim, at Sechart, Vancouver island, B.C.—by Einar Lindeman.
50. Vancouver island, B.C.—by Einar Lindeman.
51. Iron Mines, Texada island, B.C.—by E. H. Shepherd, C.E.

NOTE.—1. Maps marked thus * are out of print.

2. Maps marked thus † have been printed independently of reports, hence can be procured separately by applicants.

52. Sketch Map of Bog Iron Ore Deposits, West Arm, Quatsino sound, Vancouver island, B.C.
- *53. Iron Ore Occurrences, Ottawa and Pontiac counties, Quebec, 1908—by J. White, and Fritz Cirkel.
- †54. Iron Ore Occurrences, Argenteuil county, Quebec, 1908—by Fritz Cirkel.
- †57. The Productive Chrome Iron Ore District of Quebec—by Fritz Cirkel.
- †60. Magnetometric Survey of the Bristol mine, Pontiac county, Quebec—by Einar Lindeman.
61. Topographical Map of Bristol mine, Pontiac county, Quebec—by Einar Lindeman.
- †64. Index Map of Nova Scotia: Gypsum—by W. F. Jenkinson.
- †65. Index Map of New Brunswick: Gypsum—by W. F. Jenkinson.
- †66. Map of Magdalen islands: Gypsum—by W. F. Jenkinson.
70. Magnetometric Survey of Northernmost Arm Iron Range, Lake Timagami, Nipissing district, Ontario—by Einar Lindeman.
- †72. Brunner Peat Bog, Ontario—by A. Anrep.
- †73. Komoka Peat Bog, Ontario—by A. Anrep.
- †74. Brockville Peat Bog, Ontario—by A. Anrep.
- †75. Rondeau Peat Bog, Ontario—by A. Anrep.
- †76. Alfred Peat Bog, Ontario—by A. Anrep.
- †77. Alfred Peat Bog, Ontario: Main Ditch profile—by A. Anrep.
- †78. Map of Asbestos Region, Province of Quebec, 1910—by Fritz Cirkel.
94. Map showing Cobalt, Gowganda, Shiningtree, and Porcupine districts—by L. H. Cole, B.Sc.
95. General Map of Canada showing Coal Fields. (Accompanying report No. 83—by Dr. J. B. Porter.)
96. General Map of Coal Fields of Nova Scotia and New Brunswick. (Accompanying Report No. 83—by Dr. J. B. Porter.)
97. General Map showing Coal Fields in Alberta, Saskatchewan, and Manitoba. (Accompanying Report No. 83—by Dr. J. B. Porter.)
98. General Map of Coal Fields in British Columbia. (Accompanying Report No. 83—by Dr. J. B. Porter.)
99. General Map of Coal Field in Yukon Territory. (Accompanying Report No. 83—by Dr. J. B. Porter.)
- †106. Austin Brook Iron Bearing District, Bathurst township, Gloucester county, N.B.—by E. Lindeman.
- †107. Magnetometric Survey, Vertical Intensity: Austin Brook Iron Bearing District—by E. Lindeman.
- †108. Index Map showing Iron Bearing Area at Austin Brook—by E. Lindeman.
112. Sketch Plan showing Geology of Point Manninse, Ont.—by Professor A. C. Lane.
- †113. Holland Peat Bog, Ontario—by A. Anrep.
- 119-137. Mieu: Township Maps, Ontario and Quebec—by Hugh S. de Schmid.

NOTE.—1. Maps marked thus * are out of print.

2. Maps marked thus † have been printed independently of reports, hence can be procured separately by applicants.

- †138. Mica: Showing Location of Principal Mines and Occurrences in the Quebec Mica Area—by Hugh S. de Schmidt.
- †139. Mica: Showing Location of Principal Mines and Occurrences in the Ontario Mica Area—by Hugh S. de Schmidt.
- †140. Mica: Showing Distribution of the Principal Mica Occurrences in the Dominion of Canada—by Hugh S. de Schmidt.
- †141. Torbrook Iron Bearing District, Annapolis county, N.S.—by Howells Fréchette.
- †146. Distribution of Iron Ore Sands of the Iron Ore Deposits on the North Shore of the River and Gulf of St. Lawrence, Canada—by Geo. C. Mackenzie.
- †147. Magnetic Iron Sand Deposits in Relation to Natashkwan harbour and Great Natashkwan river, Que. (Index Map)—by Geo. C. Mackenzie.
- †148. Natashkwan Magnetic Iron Sand Deposits, Saguenay county, Que.—by Geo. C. Mackenzie.
- †152. Map Showing the Location of Peat Bogs investigated in Ontario—by A. Anrep.
- †153. Map Showing the Location of Peat Bogs investigated in Manitoba—by A. Anrep.
- †157. Lac du Bonnet Peat Bog, Ontario—by A. Anrep.
- †158. Transmission Peat Bog, Manitoba—by A. Anrep.
- †159. Corduroy Peat Bog, Manitoba—by A. Anrep.
- †160. Boggy Creek Peat Bog, Manitoba—by A. Anrep.
- †161. Rice Lake Peat Bog, Manitoba—by A. Anrep.
- †162. Mud Lake Peat Bog, Manitoba—by A. Anrep.
- †163. Litter Peat Bog, Manitoba—by A. Anrep.
- †164. Julius Peat Litter Bog, Manitoba—by A. Anrep.
- †165. Fort Francis Peat Bog, Ontario—by A. Anrep.
166. Magnetometric Map of No. 3 mine, Lot 7, Concessions V and VI, McKim township, Sudbury district, Ont.—by E. Lindeman. (Accompanying Summary Report 1911.)
- †168. Map showing Pyrites Mines and Prospects in Eastern Canada, and Their Relation to the United States Market—by A. W. G. Wilson.
- †171. Geological Map of Sudbury Nickel region, Ont.—by Prof. A. P. Coleman.
- †172. " Victoria mine—by Prof. A. P. Coleman.
- †173. " Green Hill mine—by Prof. A. P. Coleman.
- †174. " Creighton mines—by Prof. A. P. Coleman.
- †175. " showing Contact of Noritic and Laurentian in vicinity of Creighton mine—by Prof. A. P. Coleman.
- †176. " of Copper Cliff offset—by Prof. A. P. Coleman.
- †177. " No. 3 mine—by Prof. A. P. Coleman.
- †178. " showing vicinity of Stobie and No. 3 mines—by Prof. A. P. Coleman.

NOTE.—1. Maps marked thus † are out of print.


2. Maps marked thus † have been printed independently of reports, hence can be procured separately by applicants.

IN THE PRESS.

- †185. Magnetometric Survey, Vertical Intensity: Blairton iron mine, Belmont township, Peterborough county, Ontario—by E. Lindeman, 1911.
- †185a. Geological Map, Blairton iron mine, Belmont township, Peterborough county, Ontario—by E. Lindeman, 1911.
- †186. Magnetometric Survey, Belmont iron mine, Belmont township, Peterborough county, Ontario—by E. Lindeman, 1911.
- †186a. Geological Map, Belmont iron mine, Belmont township, Peterborough county, Ontario—by E. Lindeman, 1911.
- †187. Magnetometric Survey, Vertical Intensity: St. Charles mine, Tudor township, Hastings county, Ontario—by E. Lindeman, 1911.
- †187a. Geological Map, St. Charles mine, Tudor township, Hastings county, Ontario—by E. Lindeman, 1911.
- †188. Magnetometric Survey, Vertical Intensity: Baker mine, Tudor township, Hastings county, Ontario—by E. Lindeman, 1911.
- †188a. Geological Map, Baker mine, Tudor township, Hastings county, Ontario—by E. Lindeman, 1911.
- †189. Magnetometric Survey, Vertical Intensity: Ridge iron ore deposits, Wollaston township, Hastings county, Ontario—by E. Lindeman, 1911.
- †190. Magnetometric Survey, Vertical Intensity: Coehill and Jenkins mines, Wollaston township, Hastings county, Ontario—by E. Lindeman, 1911.
- †190a. Geological Map, Coehill and Jenkins mines, Wollaston township, Hastings county, Ontario—by E. Lindeman, 1911.
- †191. Magnetometric Survey, Vertical Intensity: Bessener iron ore deposits, Mayo township, Hastings county, Ontario—by E. Lindeman, 1911.
- †191a. Geological Map, Bessener iron ore deposits, Mayo township, Hastings county, Ontario—by E. Lindeman, 1911.
- †192. Magnetometric Survey, Vertical Intensity: Rankin, Childs, and Stevens mines, Mayo township, Hastings county, Ontario—by E. Lindeman, 1911.
- †192a. Geological Map, Rankin, Childs, and Stevens mines, Mayo township, Hastings county, Ontario—by E. Lindeman, 1911.
- †193. Magnetometric Survey, Vertical Intensity: Kennedy property, Carlow township, Hastings county, Ontario—by E. Lindeman, 1911.
- †193a. Geological Map, Kennedy property, Carlow township, Hastings county, Ontario—by E. Lindeman, 1911.
- †194. Magnetometric Survey, Vertical Intensity: Bow Lake iron ore occurrences, Faraday township, Hastings county, Ontario—by E. Lindeman, 1911.
- †204. Index Map, Magnetite occurrences along the Central Ontario railway—by E. Lindeman, 1911.
- †205. Magnetometric Map of Moose Mountain iron-bearing district—by E. Lindeman.

NOTE.—1. Maps marked thus * are out of print.

2. Maps marked thus † have been printed independently of reports, hence can be procured separately by applicants.

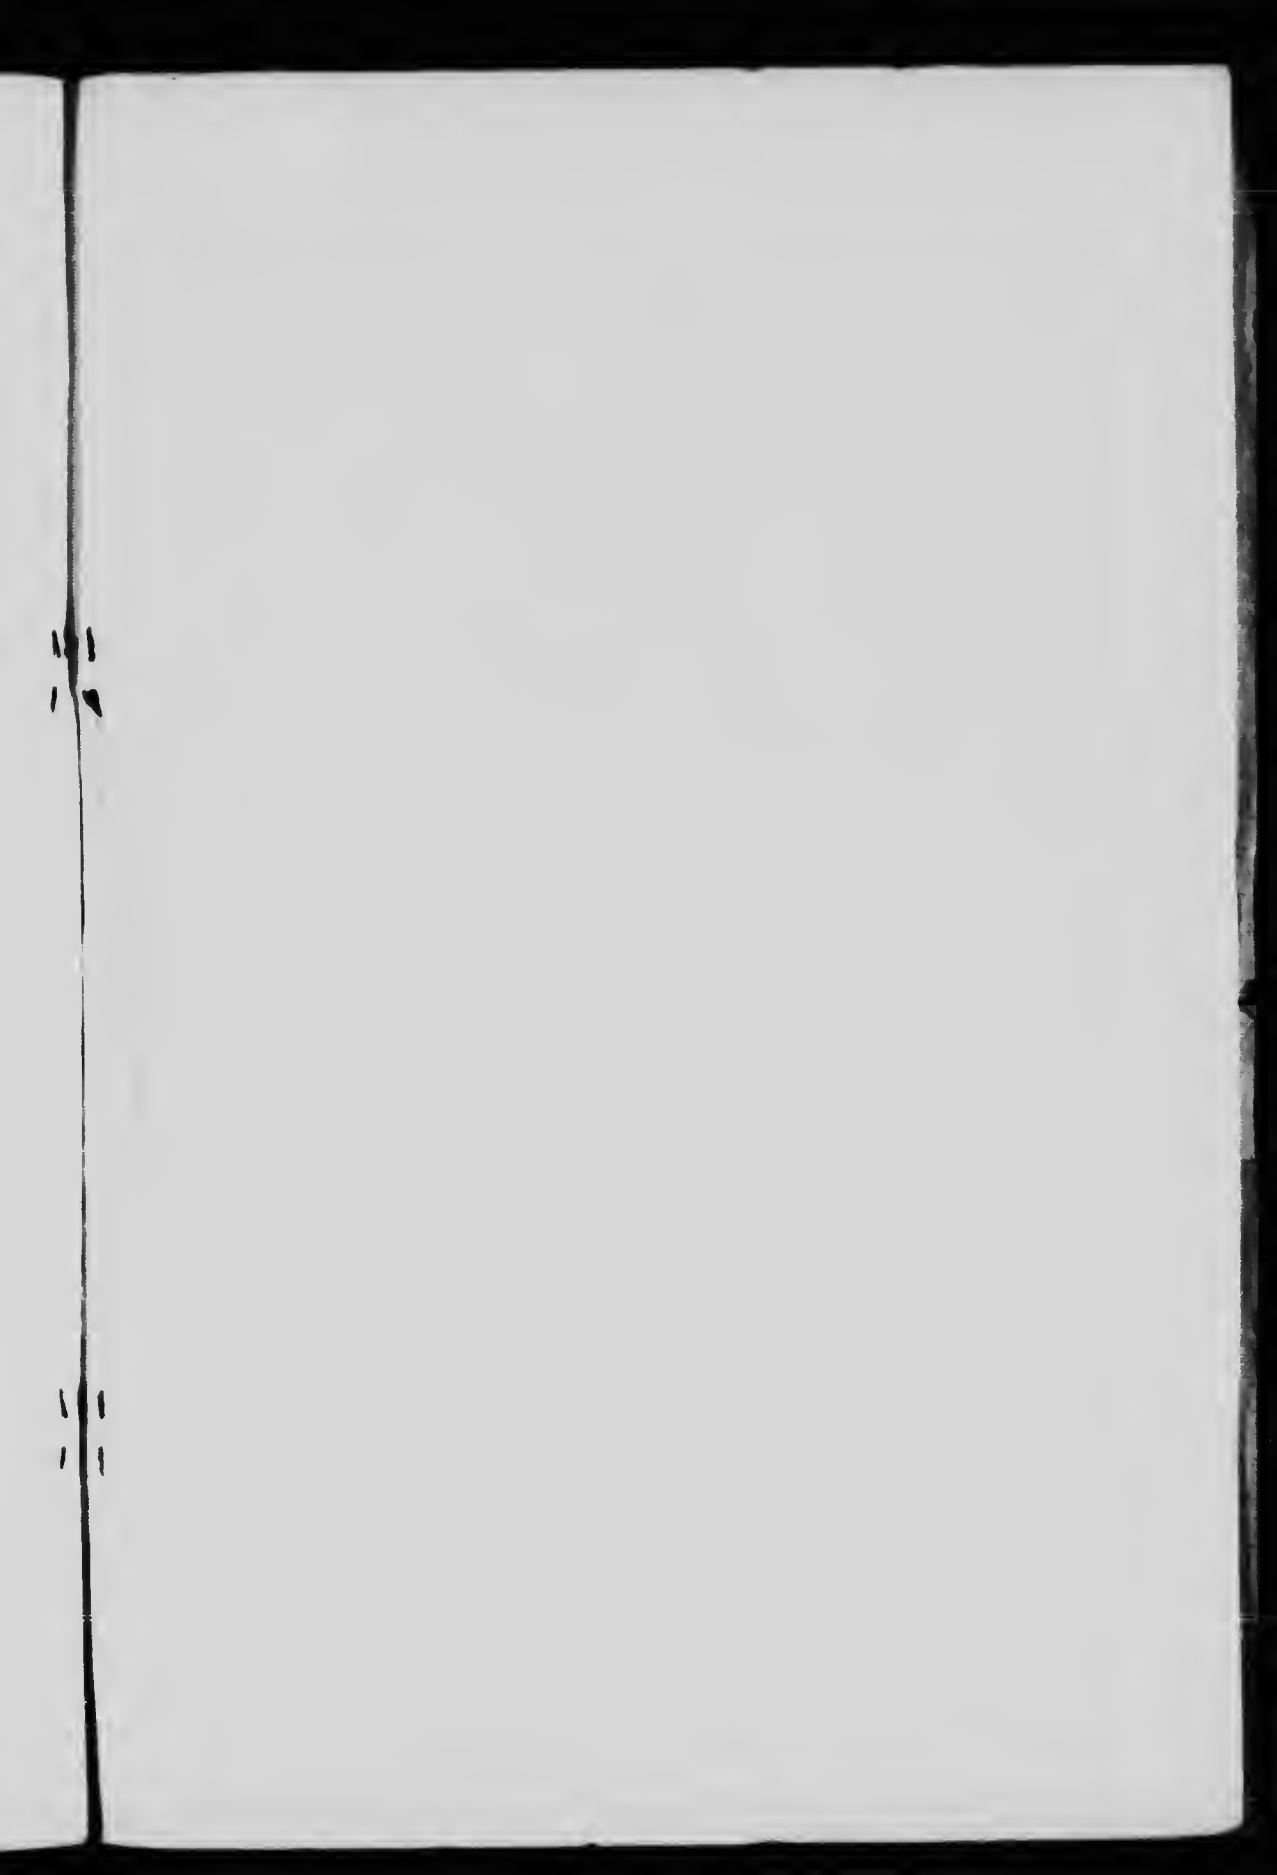




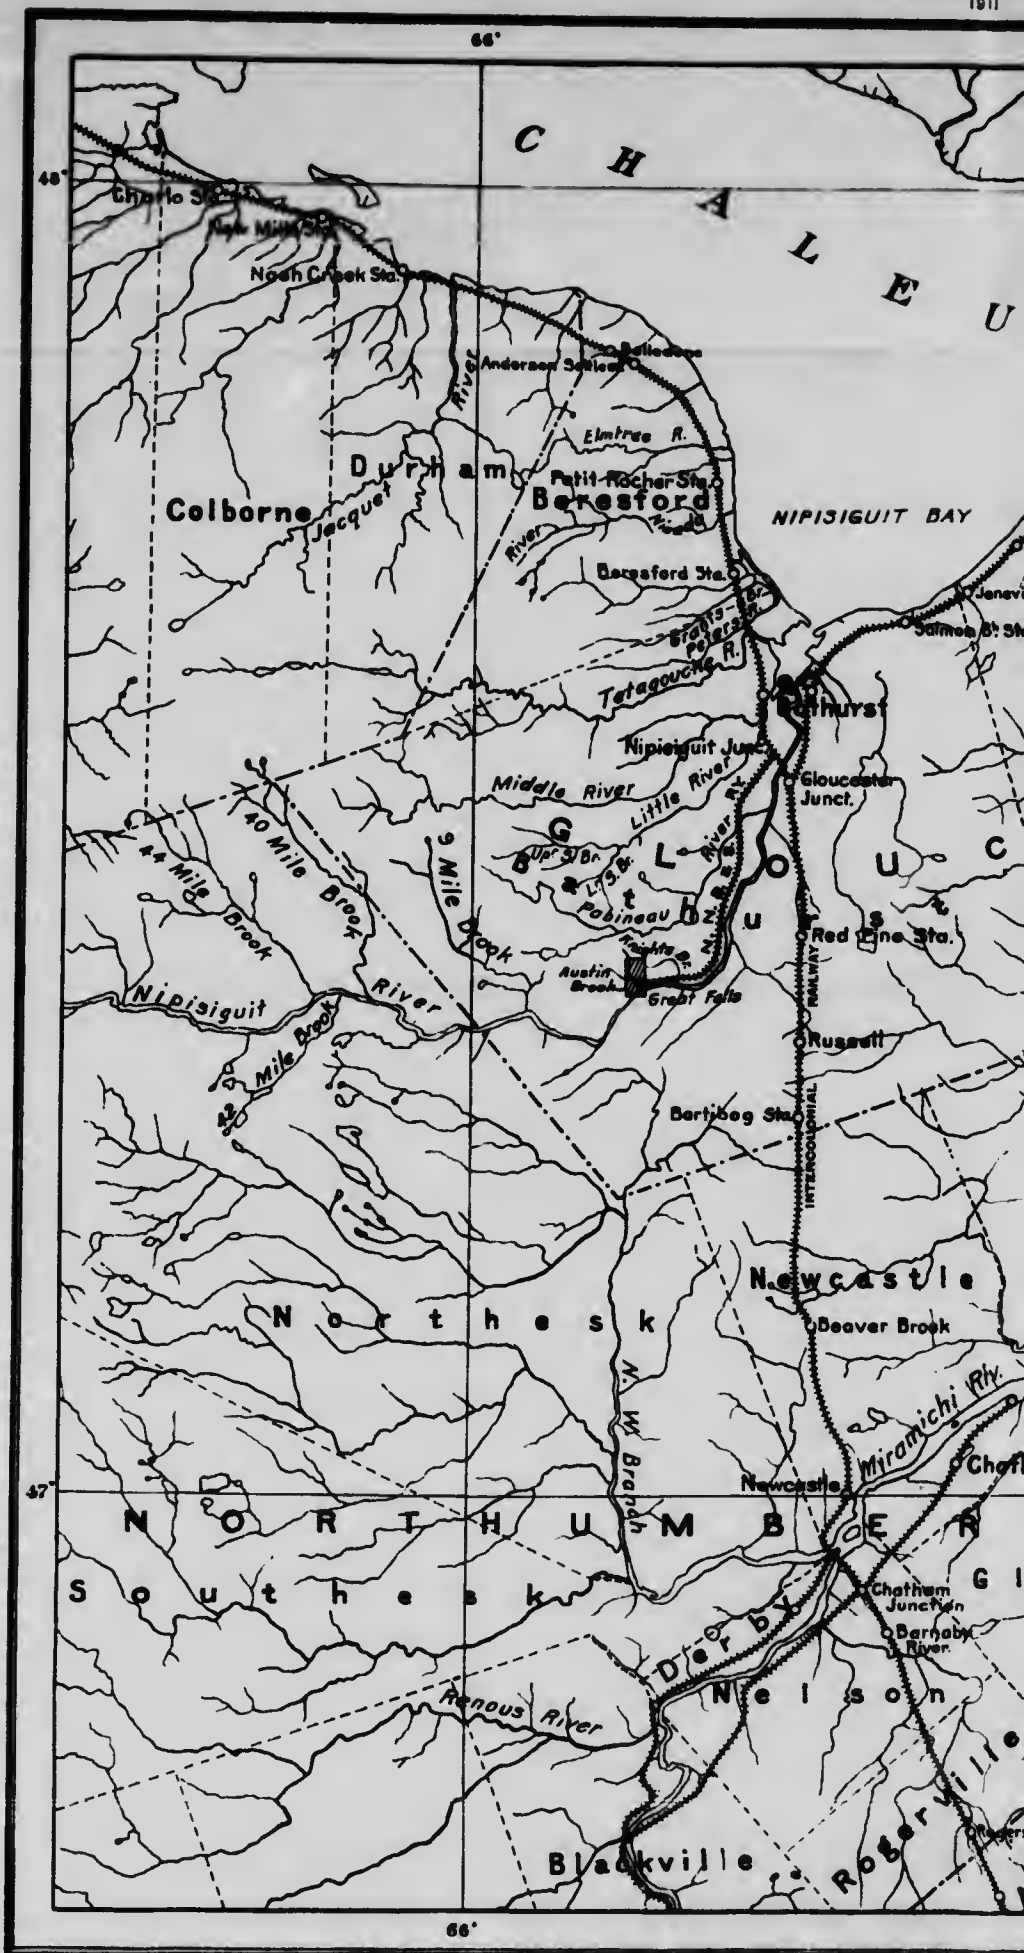


FIG 1. MAP SHOWING LOCATION OF AUSTIN
GLOUCESTER COUNTY, N.B.
Scale of Miles



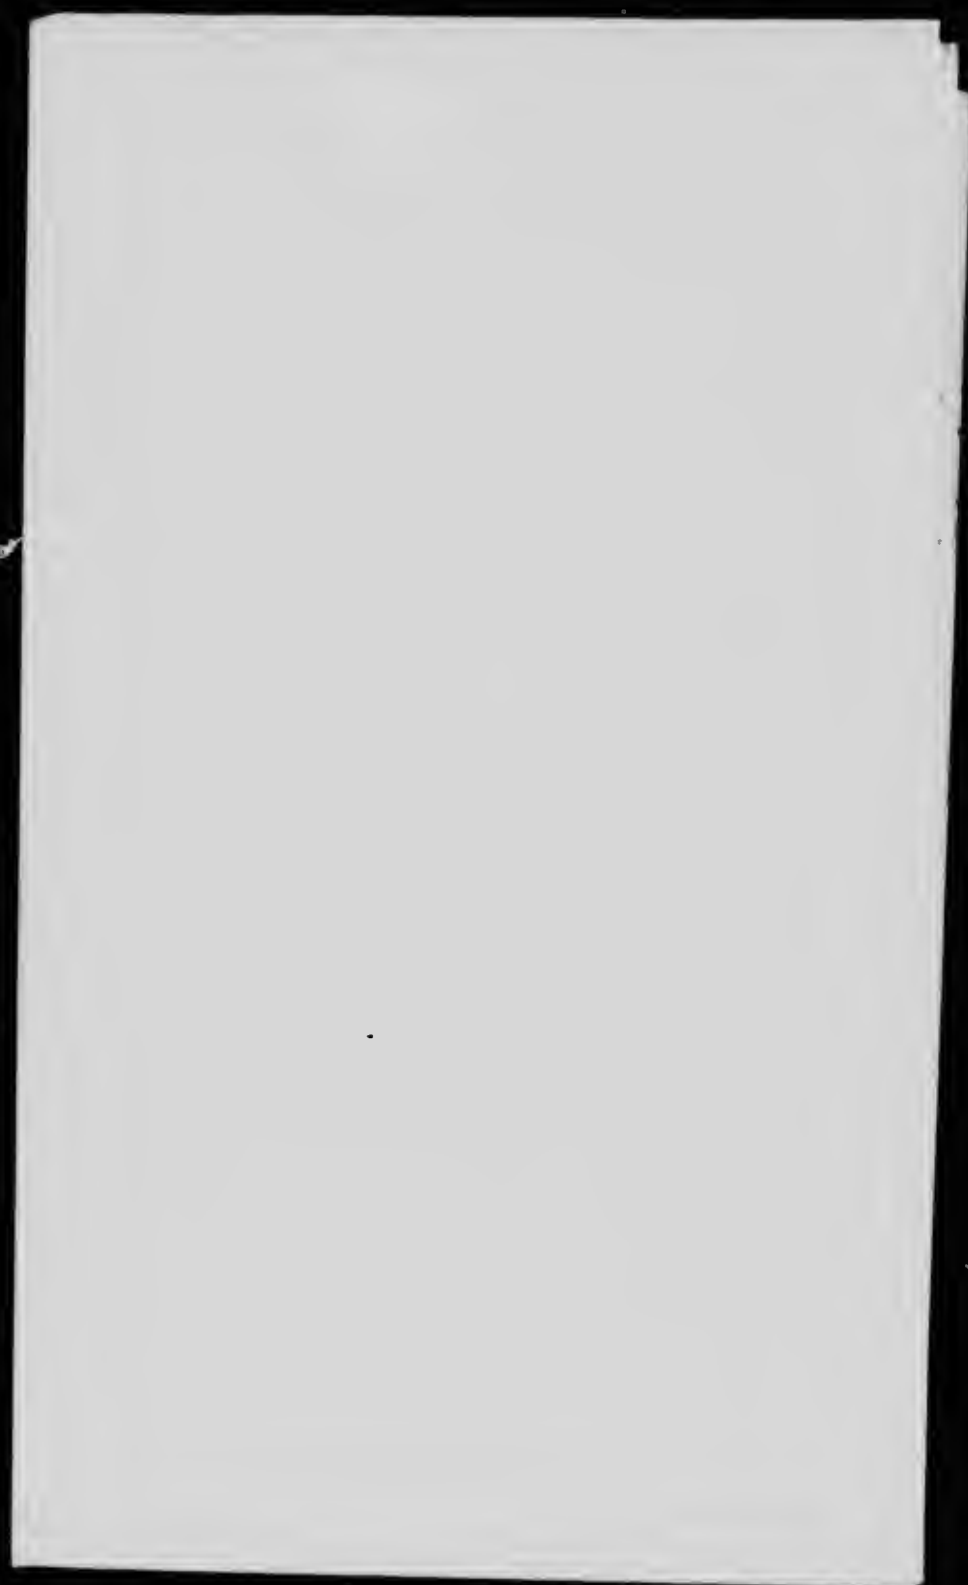

MAGNETOMETRIC MAP

LEGEND

 *Isodynamic lines of the vertical magnetic intensity*

Positive Intensity

	Magnetic Reading greater than 60°
	" " 50° to 60°
	" " 40° " 50°
	" " 20° " 40°
	" " 0° " 20°

Negative Intensity

	Magnetic Reading 0° to -20°
	" " -20° " -40°
	" " greater than -40°

Constant of Instrument = 0.8 H

 *Outcrop of ore*

 *Swamp*

 *Roads and buildings*

 *Railway*

 *Contours, interval 10 feet*

 *Bridges*

 *Reference posts*




Canada
DEPARTMENT OF MINES
MINES BRANCH

MINISTER; A.P. LOW, LL.D., DEPUTY MINISTER
EDMUND HAAHEL, PH.D., DIRECTOR

1912



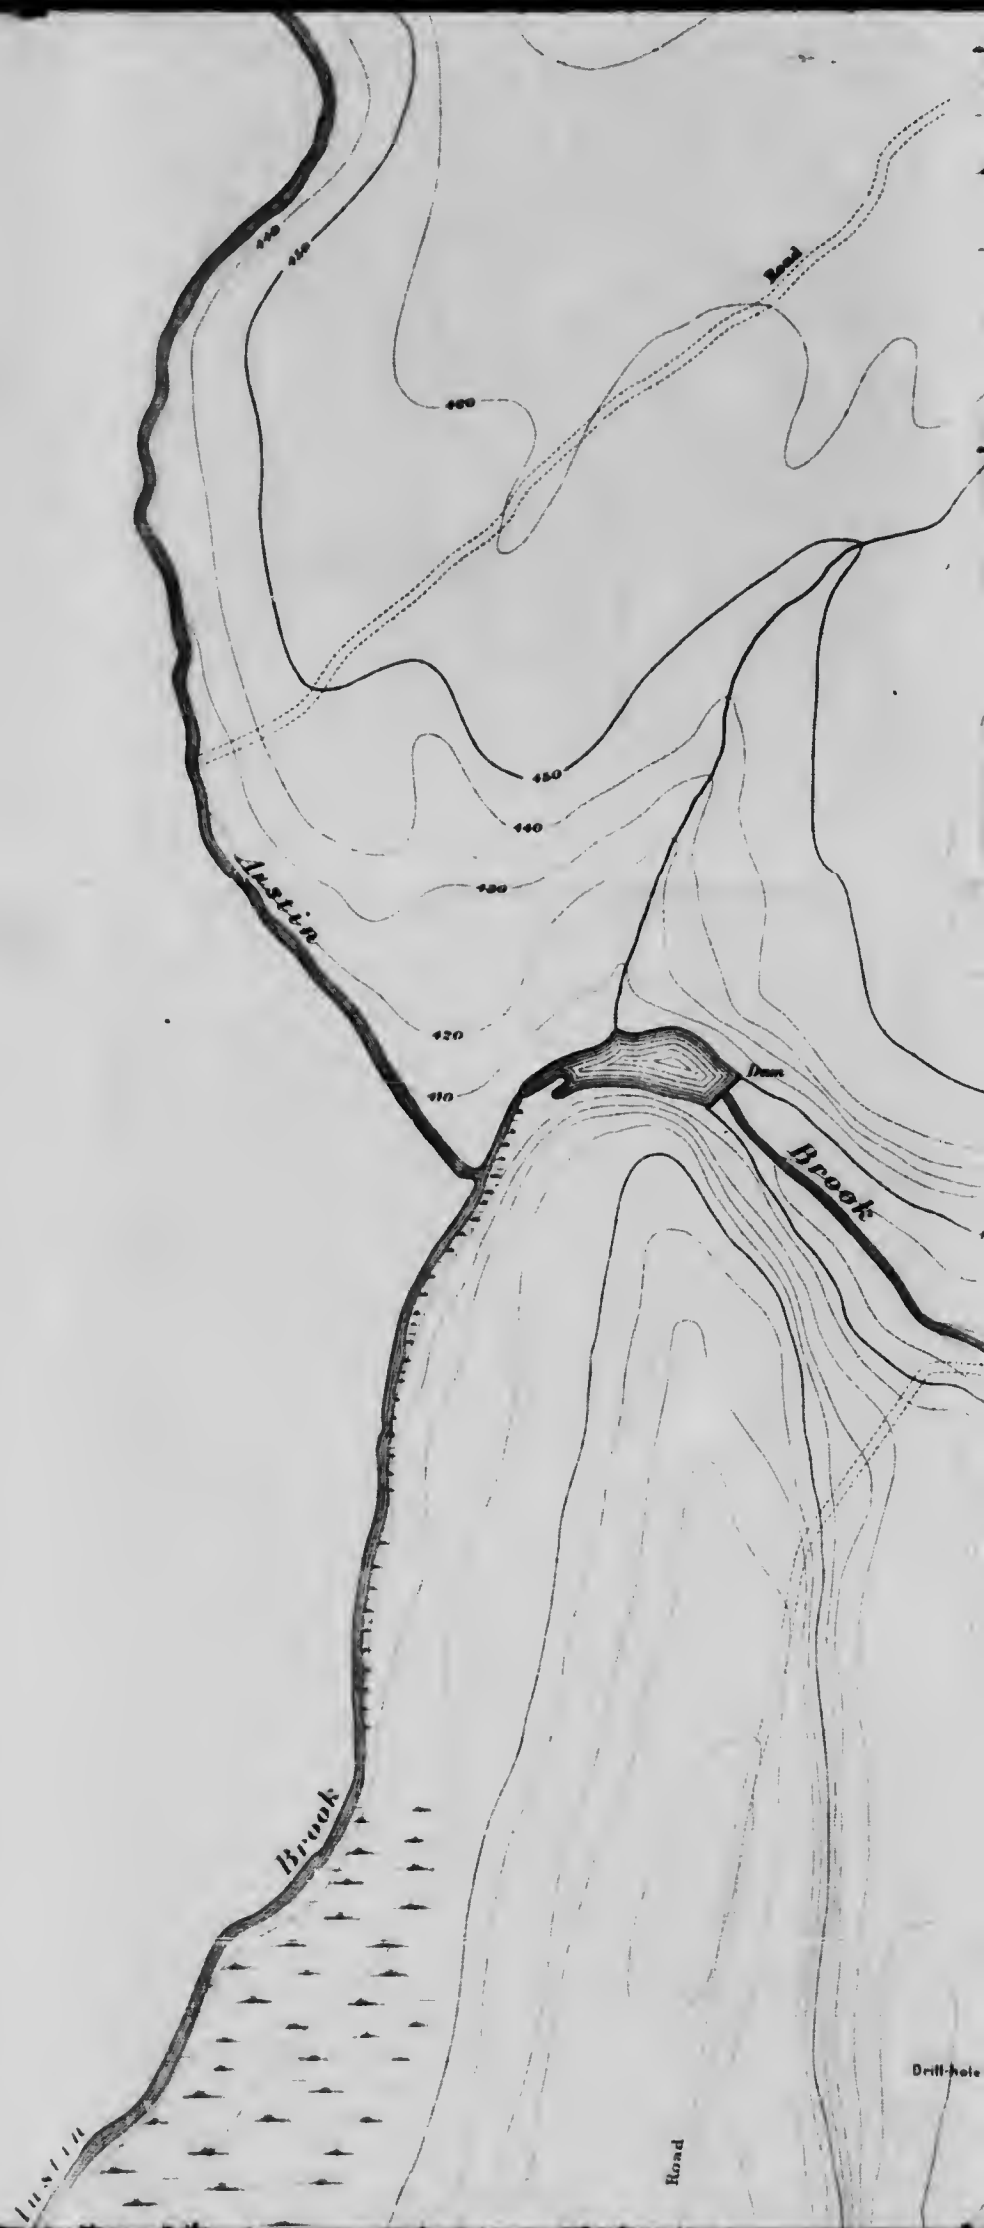





H.E. Boime, Chief Draughtsman

AUSTIN IRON BEARING GLOUCESTERVILLE NEW BRUNSWICK

Scale 400 Feet

Feet	Miles	Yards	Feet	Yards	Feet	Yards
0	0	0	100	100	100	100



To accompany Report N° 105

N° 107

TIN BROOK
TRING DISTRICT
ESTER COUNTY
W BRUNSWICK

*Surveyed by E. Lindeman
 Assisted by W. M. Morrison*

400 Feet to 1 Inch = 4800

600 800


1200 Feet





MICROCOPY RESOLUTION TEST CHART

(ANSI and ISO TEST CHART No. 2)

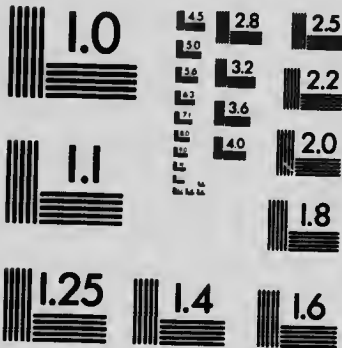

APPLIED IMAGE Inc

1653 East Main Street
Rochester, New York 14609 USA
(716) 482 - 0300 - Phone
(716) 288 - 5989 - Fax

GEOLOGICAL MAP

LEGEND

-  *Superficial deposits (peat, gravel and sand)*
-  *Outcrop of iron ore*
-  *probable ore area indicated by magnetometric survey*
-  *Quartz porphyry*
-  *Diabase*
-  *Road and buildings*
-  *Railway*
-  *Swamp*
-  *Contours, interval 10 feet.*
-  *Bridges*



da
OF MINES
RANCH


ow, LL.D., DEPUTY MINISTER
H.D., DIRECTOR





Section along line A-B

Horizontal and vertical scale, 400 feet to 1 inch

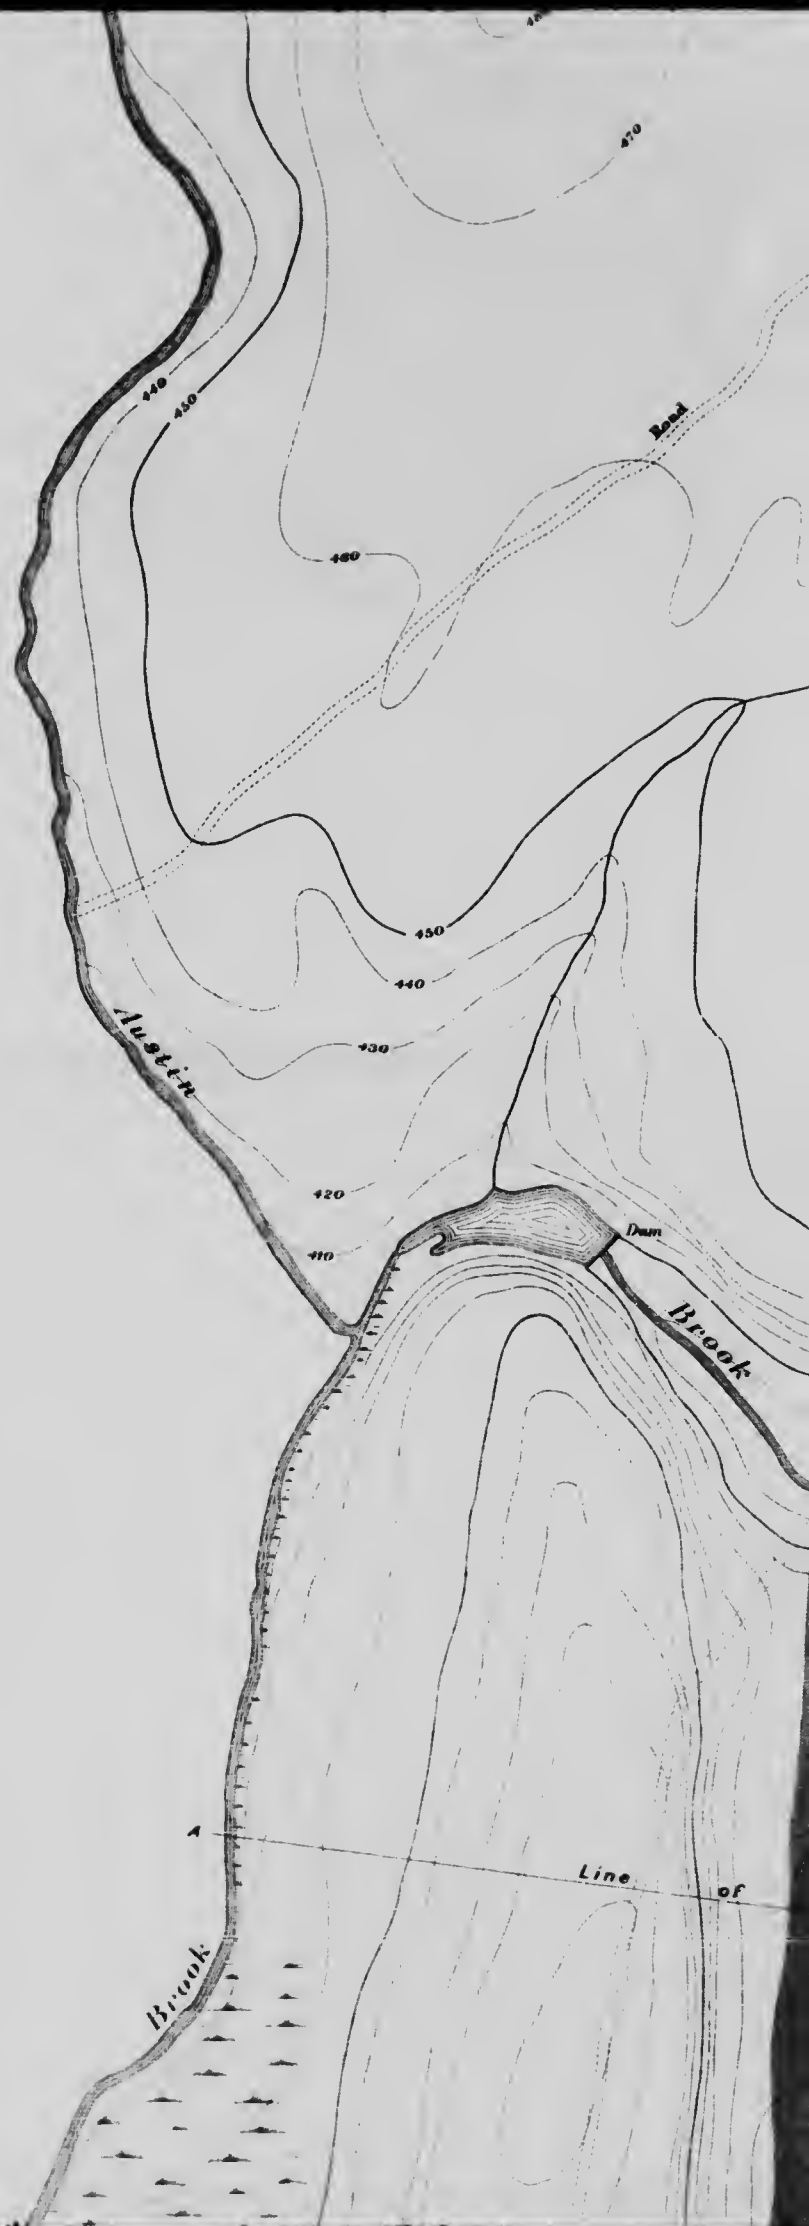






H.E. Baine, Chief Draughtsman

AUSTIN
IRON BEAR
GLOUCESTERSHIRE
NEW ENGLAND

Scale 400
 Feet 500 400 300 200 100 0

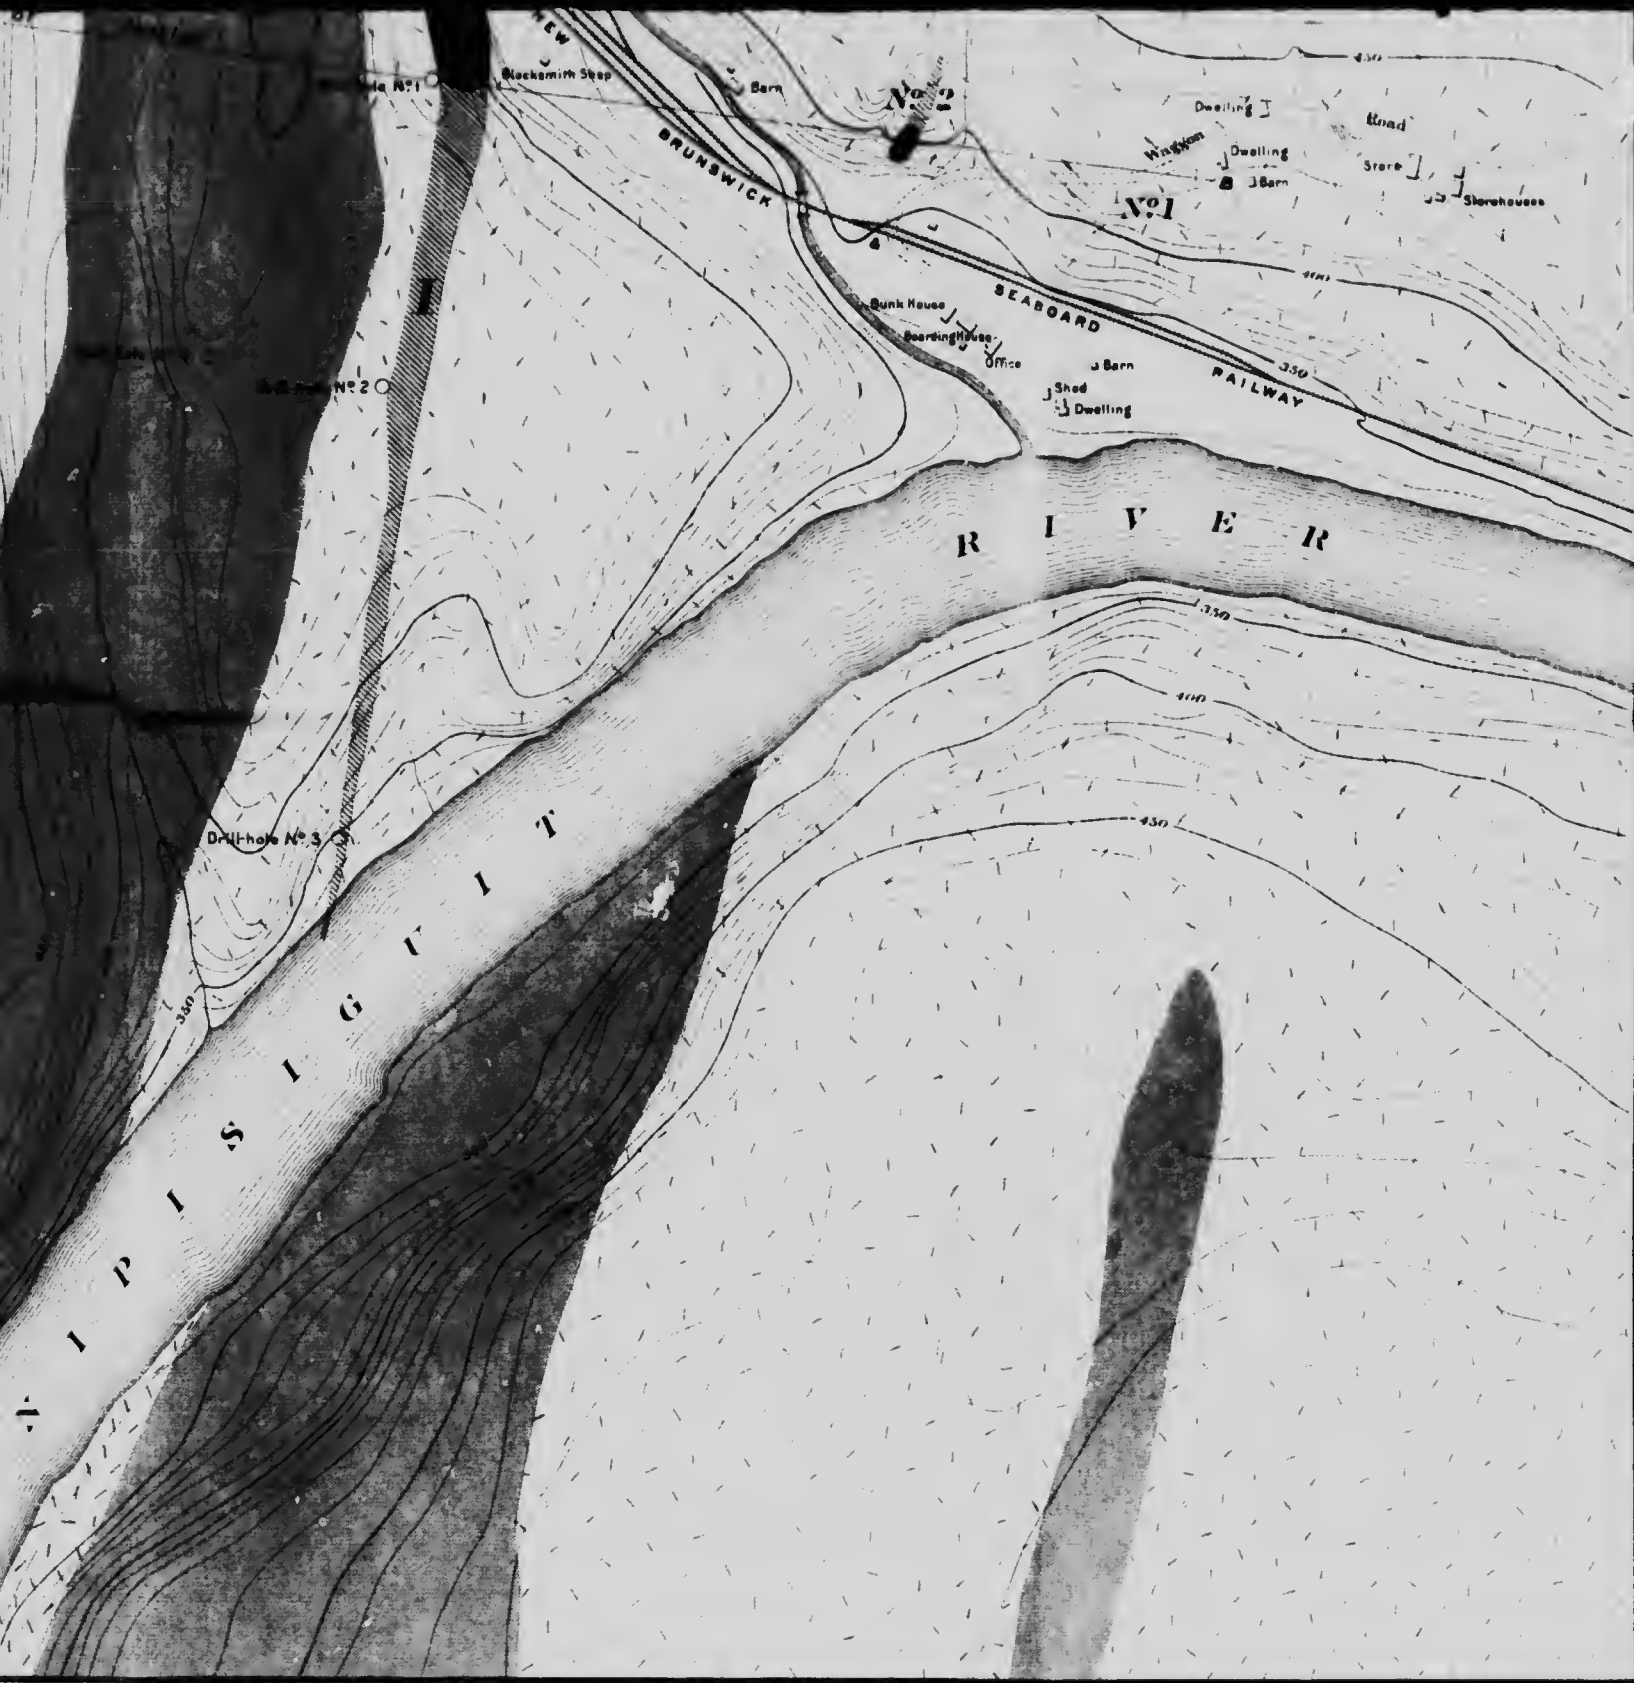

To accompany Report No. 105
No. 106

STIN BROOK
ARING DISTRICT
CESTER COUNTY
NEW BRUNSWICK

Surveyed by E. Lindeman
Assisted by W. M. Morrison

Scale 400 Feet to 1 Inch - 4866
400 800 1200 Feet

