
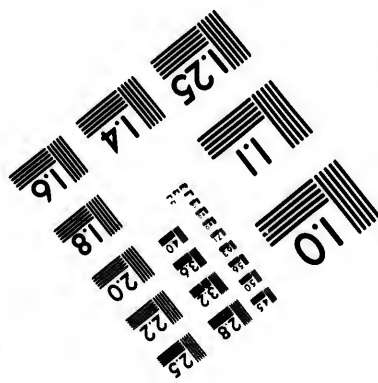
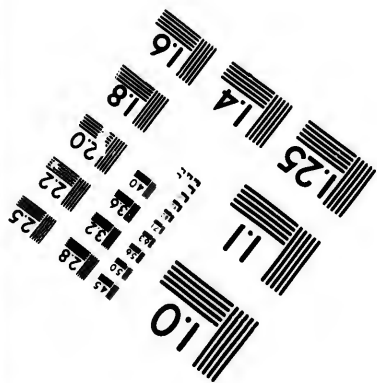



**IMAGE EVALUATION
TEST TARGET (MT-3)**

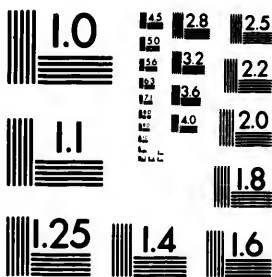

**Photographic
Sciences
Corporation**

23 WEST MAIN STREET
WEBSTER, N.Y. 14580
(716) 872-4503

15 28 25
32 22
20
8

**CIHM/ICMH
Microfiche
Series.**

**CIHM/ICMH
Collection de
microfiches.**



Canadian Institute for Historical Microreproductions / Institut canadien de microreproductions historiques

10

© 1982

Technical and Bibliographic Notes/Notes techniques et bibliographiques

The Institute has attempted to obtain the best original copy available for filming. Features of this copy which may be bibliographically unique, which may alter any of the images in the reproduction, or which may significantly change the usual method of filming, are checked below.

L'Institut a microfilmé le meilleur exemplaire qu'il lui a été possible de se procurer. Les détails de cet exemplaire qui sont peut-être uniques du point de vue bibliographique, qui peuvent modifier une image reproduite, ou qui peuvent exiger une modification dans la méthode normale de filmage sont indiqués ci-dessous.

- Coloured covers/
Couverture de couleur
- Covers damaged/
Couverture endommagée
- Covers restored and/or laminated/
Couverture restaurée et/ou pelliculée
- Cover title missing/
Le titre de couverture manque
- Coloured maps/
Cartes géographiques en couleur
- Coloured ink (i.e. other than blue or black)/
Encre de couleur (i.e. autre que bleue ou noire)
- Coloured plates and/or illustrations/
Planches et/ou illustrations en couleur
- Bound with other material/
Relié avec d'autres documents
- Tight binding may cause shadows or distortion
along interior margin/
La reliure serrée peut causer de l'ombre ou de la
distortion le long de la marge intérieure
- Blank leaves added during restoration may
appear within the text. Whenever possible, these
have been omitted from filming/
Il se peut que certaines pages blanches ajoutées
lors d'une restauration apparaissent dans le texte,
mais, lorsque cela était possible, ces pages n'ont
pas été filmées.
- Additional comments:/
Commentaires supplémentaires:

- Coloured pages/
Pages de couleur
- Pages damaged/
Pages endommagées
- Pages restored and/or laminated/
Pages restaurées et/ou pelliculées
- Pages discoloured, stained or foxed/
Pages décolorées, tachetées ou piquées
- Pages detached/
Pages détachées
- Showthrough/
Transparence
- Quality of print varies/
Qualité inégale de l'impression
- Includes supplementary material/
Comprend du matériel supplémentaire
- Only edition available/
Seule édition disponible
- Pages wholly or partially obscured by errata
slips, tissues, etc., have been refilmed to
ensure the best possible image/
Les pages totalement ou partiellement
obscurcies par un feuillet d'errata, une pelure,
etc., ont été filmées à nouveau de façon à
obtenir la meilleure image possible.

This item is filmed at the reduction ratio checked below/
Ce document est filmé au taux de réduction indiqué ci-dessous.

10X	14X	18X	22X	26X	30X
<input type="checkbox"/>	<input type="checkbox"/>	<input type="checkbox"/>	<input checked="" type="checkbox"/>	<input type="checkbox"/>	<input type="checkbox"/>
12X	16X	20X	24X	28X	32X

The copy filmed here has been reproduced thanks to the generosity of:


Nova Scotia Public Archives

The images appearing here are the best quality possible considering the condition and legibility of the original copy and in keeping with the filming contract specifications.

Original copies in printed paper covers are filmed beginning with the front cover and ending on the last page with a printed or illustrated impression, or the back cover when appropriate. All other original copies are filmed beginning on the first page with a printed or illustrated impression, and ending on the last page with a printed or illustrated impression.

The last recorded frame on each microfiche shall contain the symbol \rightarrow (meaning "CONTINUED"), or the symbol ∇ (meaning "END"), whichever applies.

Maps, plates, charts, etc., may be filmed at different reduction ratios. Those too large to be entirely included in one exposure are filmed beginning in the upper left hand corner, left to right and top to bottom, as many frames as required. The following diagrams illustrate the method:

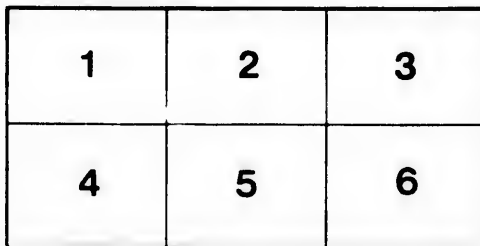

L'exemplaire filmé fut reproduit grâce à la générosité de:


Nova Scotia Public Archives

Les images suivantes ont été reproduites avec le plus grand soin, compte tenu de la condition et de la netteté de l'exemplaire filmé, et en conformité avec les conditions du contrat de filmage.

Les exemplaires originaux dont la couverture en papier est imprimée sont filmés en commençant par le premier plat et en terminant soit par la dernière page qui comporte une empreinte d'impression ou d'illustration, soit par le second plat, selon le cas. Tous les autres exemplaires originaux sont filmés en commençant par la première page qui comporte une empreinte d'impression ou d'illustration et en terminant par la dernière page qui comporte une telle empreinte.

Un des symboles suivants apparaîtra sur la dernière image de chaque microfiche, selon le cas: le symbole \rightarrow signifie "A SUIVRE", le symbole ∇ signifie "FIN".

Les cartes, planches, tableaux, etc., peuvent être filmés à des taux de réduction différents. Lorsque le document est trop grand pour être reproduit en un seul cliché, il est filmé à partir de l'angle supérieur gauche, de gauche à droite, et de haut en bas, en prenant le nombre d'images nécessaire. Les diagrammes suivants illustrent la méthode.

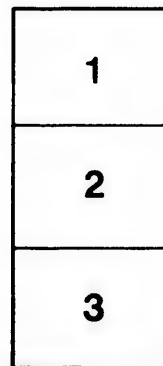

ART. III.—FEATHER-ALUM (HALOTRICHITE) FROM GLACE BAY,
CAPE BRETON. BY E. GILPIN, F. G. S., F. R. S. C.
CHIEF INSPECTOR OF MINES.

(*Read March 9th, 1885.*)

DURING a visit to the Glace Bay Coal Mines, in Cape Breton County, I had specimens of Melanterite, or Green Vitriol, and a few pieces of a white fibrous mineral brought to me from some heaps of shale and slack coal, which were being removed from the pit. The former mineral is not unfrequently met with, the latter being new to me I made two analyses of it, and thought that the results might interest some of the members of the Institute.

The mineral is of a white colour, turning brown on exposure, and of a delicate fibrous structure. It is soluble in water and

The analyses gave:

Protoxide of Iron..	16.570
Alumina..	9.131
Sulphuric Acid..	39.715
Water..	35.097
Silica..	Traces
Magnesia..	do
Lime..	do

100.513

This analysis, while not agreeing exactly with any given in Dana's mineralogy, would apparently place the mineral in the Halotrichite group.

The following table shews the composition of a number of specimens of Halotrichite compared with that of the mineral under consideration.

AK
QE
P11
no. 7

Locality.	Sulphuric Acid.	Alumina.	Ferrous. Oxide.	Water.
Moorfield . . .	36.03	10.91	9.37	42.03
Hurlet	35.60	7.12	13.56	43.71
"	30.90	5.20	20.70	43.20
"	28.63	2.85	19.35	48.58
Freyenwalde	43.90	15.25	7.50	33.10
Glace Bay . . .	39.71	9.13	16.57	35.09

It would be interesting to know how much time was occupied in the formation of this mineral at the Glace Bay Mines, some of the fibres being one-third of an inch in length. It can, however, only be remarked that the gallery in which it occurred had been excavated about twelve years ago.

Another hydrous sulphate, found as a product of decomposition in Coal Mines, is known as Alunogen.

The following analysis of a specimen occurring as an efflorescence at the Scotia Mine in Cumberland County, is taken from the report of the Canadian Geological Survey for the year 1878-79.

Sulphuric Acid	36.935
Alumina	13.479
Ferrie Oxide	2.888
Ferrous Oxide157
Water	45.109
Lime140
Magnesia138
Potash087
Sulphur131
Insoluble235

99.299

Some years ago a hydrous sulphate of Alumina and Magnesia of similar origin was found on Silurian Slates at Newport, and was shown by the late Professor How to be identical with Pickeringite, a mineral up to that time known only in Peru.

Melanterite, the first of the minerals mentioned in this paper, belongs to the Copperas group, which contains among its more noteworthy species, the hydrous sulphates of Iron, Zinc, and Copper. The first named occurs in nature as a product of the decomposition of iron pyrites, and is largely made from the waste oil of vitriol from wire and galvanising works, with scrap iron, and from alum shale. The production of Copperas in the United States in the year 1882 was estimated at 15,000,000 pounds, valued at three quarters of a cent per pound. It is largely used by tanners and dyers on account of its forming a black colour with tannic acid. It is also used in paper mills, bleacheries, paint and ink manufactories, and as a disinfectant.

White Vitriol is a similar compound, formed naturally from the oxidation of Zinc Sulphide, and commercially by the action of Sulphuric acid on Zinc. As met in the Arts, White Vitriol is a form made by melting the Crystallised Sulphate and agitating it until it cools in a granular state.

Blue or Copper Vitriol is used in many dyeing and other chemical operations. When it occurs in nature in solution, as in the water flowing from copper lodes, large quantities of the metal are obtained by exposing it to the action of iron, when it is precipitated as a red mud, easily smelted and refined.

The minerals Feather-Alum and Pickeringite mark further steps in this chemical action of air and moisture on Sulphur. They may, broadly speaking, be considered as belonging to the native Alum group, the members of which contain water and sulphate of Alumina and some other sulphate. In Potash Alum, the common Alum of the shops, this other sulphate is a sulphate of potash. The corresponding sulphate in the other Alums is that of Soda, Magnesia, Ammonium, Iron or Manganese, and finally we have Alumogen, already referred to, a simple hydrous sulphate of Alumina.

We have already remarked on the formation of Sulphate of Iron by the oxidation of iron pyrites. When this action takes place in the presence of clays, largely composed of Silicate of Alumina, part of the Sulphuric Acid unites with the Alumina, and the commonest resulting form is that of a hydrous sulphate

of Iron and Alumina, such as the mineral forming the subject of this paper. As the alkalies are frequently present in appreciable quantities in clays, true Potash or Soda Alums are often formed.

When clay slates are impregnated with these sulphates they are termed Aluminous, and are sometimes rich enough to yield Alum on the commercial scale. The following outline of the process is from Dana's Mineralogy, p. 128. The rock is first slowly heated, after piling it in heaps, in order to decompose fully the pyrites, and transfer the Sulphuric Acid of any Sulphate of Iron to the Alumina, and thus produce the largest amount possible of Sulphate of Alumina. It is next lixiviated in stone cisterns. The lye containing this sulphate is afterwards concentrated by evaporation, and then the requisite proportion of Potash (sulphate or chloride, alum containing potash as well as alumina) is added to the liquid. A precipitate of Alum falls which is afterwards washed and crystalised. In France Ammoniacal Salts are used instead of Potash, and an Ammoniacal Alum is formed.

At Whitby, in Yorkshire, the business of Alum making is a very old one, having been commenced by Sir Thomas Challoner in 1460, who brought workmen from France where the process had long been kept secret as a privilege of the ecclesiastical powers. The Alum shale occurs in strata of Liassic age, and is overlaid by a hard compact stone, known locally as "dogger." The Shale bed is about 200 feet thick, and is a hard bluish gray shaly clay which rapidly crumbles on exposure. The whole deposit abounds in iron pyrites, but only the richer portions are excavated for treatment. About 65 tons of the Shale yield a ton of Alum. It would unduly extend the limits of this paper to give the full details of the manufacture, which is based on that already outlined.

In the United States there are no deposits of Alum Shale of any commercial value, but the salt is manufactured to the extent of 20,000 tons annually, valued at about \$800,000. It is nearly all made from alum clays imported from France and England. The process of manufacture is very simple and consists in mixing the Alum Shale with Sulphuric Acid, dissolving out the resulting

Sulphate of Alumina, adding an Alkali Sulphate and crystallising the resulting salt.

Domestic records show that through long ages the natural supplies of Copperas and Alum equalled the demands of the dyer and manufacturer. When this source was no longer adequate the chemist showed how the slow operations of nature could be hastened, and now these useful chemicals are produced with readiness, and at a price formerly deemed unattainable.

These minerals, however, are highly interesting from a different stand-point. Hitherto we have regarded them as the source of agents which have become indispensable to our comfort, and literally the foundation of many of the varied hues that man affects in his dress. But the study of their origin and natural transmutations give an instructive insight into some of the changes that are continually going on in the earth. We see them marking several of the alterations which have led to the disintegration of rocks, the formation of soils, of economic ores, etc.

In conclusion I may mention that the manufacture of these commercial Salts has not been undertaken in Canada. The total value of textile fabrics, which may call for various processes of dyeing, manufactured in the Dominion, was according to the last census nearly \$20,000,000.

There would therefore appear to be a field for the manufacture of these Copperas and Alum Salts, in this country, and some of the shales of our coal fields may be found well adapted for the purpose.

